




ETHYLENE-TETRAFLUOROETHYLENE COPOLYMER

Contents		
<b>1</b>	<b>Fluon®ETFE and its Grades</b>	<b>2</b>
<b>2</b>	<b>Thermal Properties</b>	<b>3</b>
2-1	Heat Aging	3
2-2	Linear Thermal Expansion Coefficient	3
2-3	Heat Distortion Temperature	3
2-4	Flammability	4
2-5	Thermal Decomposition	4
2-6	Summary of Thermal Properties	4
<b>3</b>	<b>Mechanical Properties</b>	<b>5</b>
3-1	Tensile Properties	5
3-2	Tensile Creep	9
3-3	Compression Properties	10
3-4	Flexural Properties	11
3-5	Impact Strength	12
3-6	Surface Hardness	13
3-7	Friction and Wear Properties	13
3-8	Mechanical Properties of Various Plastics	15
<b>4</b>	<b>Electrical Properties</b>	<b>16</b>
4-1	Dielectric Properties	16
4-2	Insulation	18
4-3	Arc Resistance	18
4-4	Tracking Resistance	19
4-5	Cut-through Resistance	19
<b>5</b>	<b>Chemical Properties</b>	<b>20</b>
5-1	Chemical Resistance	20
5-2	Chemical Stress Crack	23
5-3	Weatherability	23
5-4	Hot Water Resistance	24
5-5	Gas Permeation and Moisture Permeation	25
5-6	Light Transmittance	25
5-7	Radiation Resistance	26
5-8	Food Safety	27
<b>6</b>	<b>Physical properties of Fluon®ETFE</b>	<b>28</b>
<b>7</b>	<b>Molding of Fluon®ETFE</b>	<b>29</b>
7-1	Raw Resin and Handling	29
7-2	Injection Molding	31
7-3	Extrusion Molding	34
7-4	Powder Coating	35
7-5	Other Processing Methods	36



## Fluon®ETFE and its Grades

Fluon®ETFE is a thermoplastic fluoropolymer developed by Asahi Glass. It is a copolymer comprised of tetrafluoroethylene (C<sub>2</sub>F<sub>4</sub>) and ethylene (C<sub>2</sub>H<sub>4</sub>) and has the following basic structure:

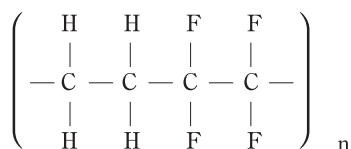

Fluon®ETFE has electrical properties and chemical resistance comparable to those of typical fluoropolymers such as polytetrafluoroethylene (PTFE) and tetrafluoroethylene-hexafluoropropylene copolymer (FEP), yet at the same time, is characterized by improved mechanical properties and outstanding processability.

This technical brochure provides data on various characteristics of Fluon®ETFE, as well as data on

processing, obtained at the laboratories of Asahi Glass-information that, hopefully, may serve as reference for the development of various applications for Fluon®ETFE.

Notice: All data given herein are measured values, believed to be accurate, but are presented without guarantee, warranty, or responsibility expressed or implied.

Plastics are expressed as abbreviations in text, tables, and figures. The names are as follows:

FEP: tetrafluoroethylene-hexafluoropropylene  
 PVdF: polyvinylidene fluoride  
 PCTFE: polychlorotrifluoroethylene  
 PE: polyethylene  
 PC: polycarbonate  
 PVC: Polyvinyl chloride  
 HDPE: high-density polyethylene

**Table 1 Grades of Fluon®ETFE (Natural)**

Grade	Melt Flow Rate*1	Melt index*2	Characteristic	APPLication	Molding Method
C-55AP	3.9~6.5	1~2	standard	General	extrusion molding
C-88AP	9.0~12.0	3~4	standard	General	extrusion molding, injection molding
C-55AXP	3.9~6.5	1~2	stress-crack resistant	wire cover	extrusion molding
C-88AXP	9.0~12.0	3~4			extrusion molding, injection molding
C-88AXMP	27~43	10~16	high fluidity	thin wire cover, Lighth gate	extrusion molding, injection molding

\*1 Melt flow rate in accordance with ASTM D 3159 (297°C, 5,000gf)

\*2 Melt index in accordance with ASTM D 1238 (300°C, 2, 160gf)

**Table 2 Grades of Fluon®ETFE (powder)**

Grade	Molded Thickness	Molding Method	Characteristic and Usage
Z-8820X	50~80μm	static powder coating	non-sticking for cookware
Z-885C	50~150μm	static powder coating	non-sticking roll etc.
	50~400μm	fluid dipping coating	corrosion-proof plant machinery
ZL-520N	~1 mm	static powder coating (over coat)	corrosion-proof with 20% carbon
ZL-521N	30~50μm	static powder coating	for over-coating on ZL-520 contains 5% carbon fiber
ZL-522F	2~5 mm	rotolining	corrosion proof for severe conditions reactor, tank, line, pump, tank-trunk
TL-581	2~5mm	rotolining	
TL-081	~1 mm	static and fluid dipping coating (over coat)	



## Thermal Properties of Fluon®ETFE

### 2-1 Heat Aging

Fluon®ETFE is a crystalline thermoplastic with a melting point in the range of 265~270°C. In general, however, it is practical to use Fluon®ETFE at a continuous service temperature determined by the long-term change of tensile elongation, which accurately reflects thermal deterioration of the polymer. For Fluon®ETFE, C-88AP and C-55AP grades, the elongation value is reduced to half of the original value, after 10 years (100 thousand hours) at 150 °C.

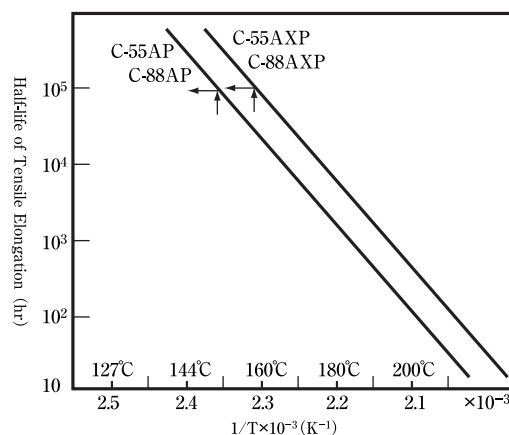


Figure 1 Half-life of Elongation and Temperature

### 2-2 Linear thermal expansion coefficient

The thermal expansion and contraction of polymers are crucial when using polymers as industrial materials, or when designing molds for processing.

Table 4 Linear Thermal Expansion Coefficient of Plastics

ASTM D696 (temp. range : room temperature~60°C)

Polymers	Fluon®ETFE		PTFE	PFA	FEP	ECTFE	PVDF	PVF	PE	PVC	PC
	C-88AP	C-88AXP									
Linear Thermal Expansion Coeff. 10 <sup>-5</sup> /°C	9~14	9~14	9~11	11~13	8~11	9~11	3~6	5~8	11~13	7~12	6~8

### 2-3 Heat Distortion Temperature

The heat distortion temperature represents the temperature at which the test sample bends by 0.254 mm with 4.6 or 18.6 kg/cm<sup>2</sup> of load applied, and temperature increased at the rate of 2 °C/min. The degree of deformation is only slight, and as result, the value merely gives a general idea of the polymer's heat resistance.

Table 5 Heat Distortion Temperature of Plastics Heat Distortion

ASTM D648

Polymers		Fluon®ETFE		PTFE	PFA	FEP	ECTFE	PVDF	PVF	PE	PVC	PC
		C-88AP	C-88AXP									
Heat Distortion Temperature °C	4.6 kg/cm²	90	80	120	70	70	90~115	150~156	—	60~80	55~75	144
	18.5 kg/cm²	50	50	50	50	50	66~76	95~100	—	—	—	135

## 2-4 Flammability

Although Fluon®ETFE has C<sub>2</sub>H<sub>4</sub> units in the main chain, according to evaluations by UL standard subject 94, it has a 94V-0 flammability. Results of ASTM D 165 also show that it is noncombustible. Furthermore, the oxygen index based on ASTM D 2863 is 32%

## 2-5 Thermal Decomposition

The termination temperature of weight-decrease, when the temperature is raised at the rate of 10°C/min, is in the range of 350~360°C in air, as shown in Figure 2, and 390~400°C in nitrogen. The activation energy of thermal decomposition is about 30 kcal/mol in air, and about 55 kcal/mol in nitrogen.

Therefore, at normal molding temperature, thermal decomposition does not occur. However, even around 300°C, if maintained for a long period of time, weight loss due to decomposition occurs. In such situation, the gas generated by decomposition consists mostly of hydrogen fluoride.

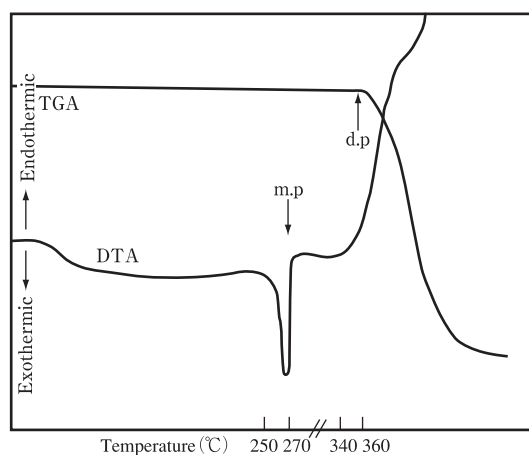


Figure 2 Differential Thermal Analysis and Heated Weight Loss

## 2-6 Summary of Thermal Properties

Table 6 Thermal Properties of Fluon®ETFE

Subject	Unit	Property	Method
Specific Heat	cal/g°C	0.3	
Thermal Conductivity	cal/cm sec°C	$4 \times 10^{-4}$	C177
Heat of Fusion	cal/g	10~12	—
Linear Thermal Expansion Coefficient	cm/cm°C (-30~+100°C)	$9 \sim 14 \times 10^{-5}$	D696
Heat Distortion Temperature	4.6kg/cm <sup>2</sup> °C	92~95	D648
	18.6kg/cm <sup>2</sup> °C	63~67	D648
Fragility Temperature	°C	-125	D764
Flammability		NB (noncombustible) 94V-0	D635 UL
Oxygen Index	%	32	D2863



## Mechanical Properties of Fluon®ETFE

Fluon®ETFE have balanced tensile elongation and strength as well as toughness, ensuring no breakage by impact at room temperature.

### 3-1 Tensile Properties

Figures 3 and 4 show the tensile strength and elongation in relation to temperature. Figure 5 shows the relationship between tensile strength and elongation of various plastics.

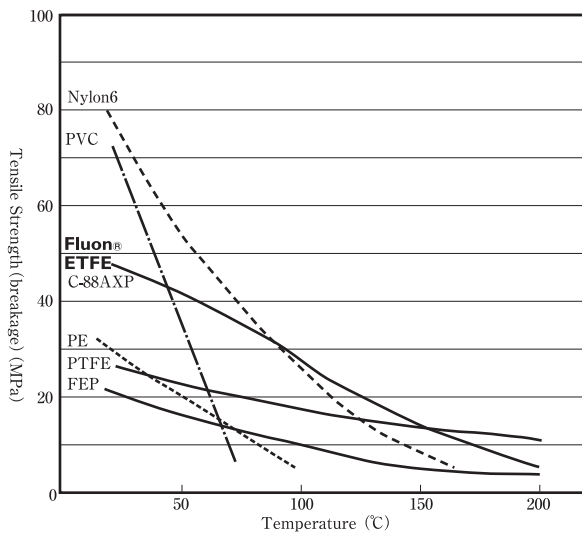


Figure 3 Effect of Temperature on Tensile Strength

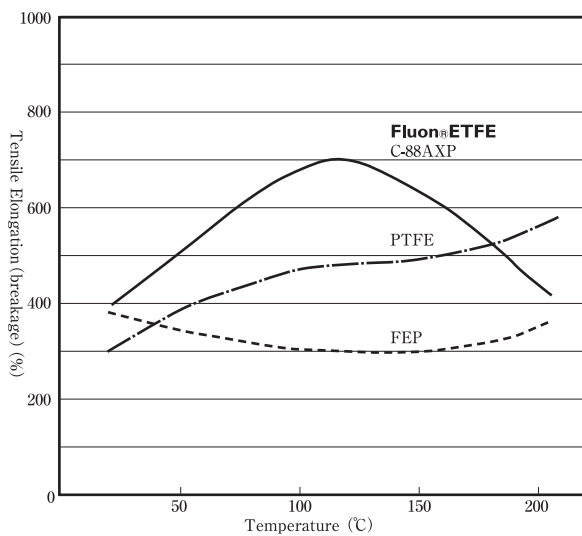


Figure 4 Effect of Temperature on Tensile Elongation

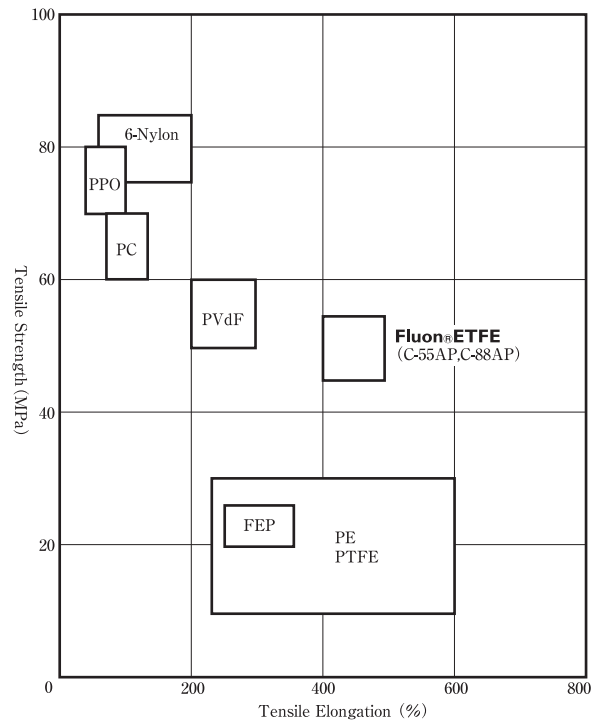


Figure 5 Strength vs. Elongation for Various Plastics

### C-55AP

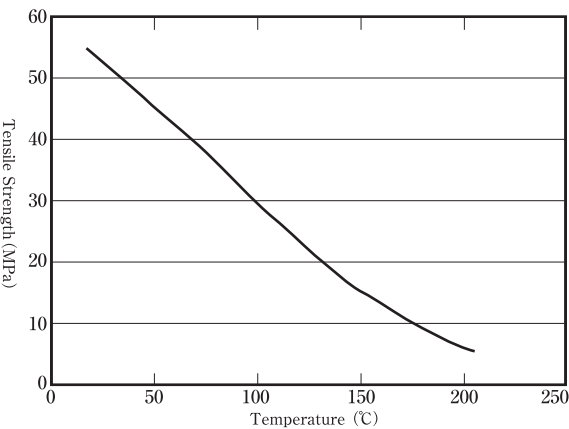


Figure 6 Effect of Temperature on Tensile Strength

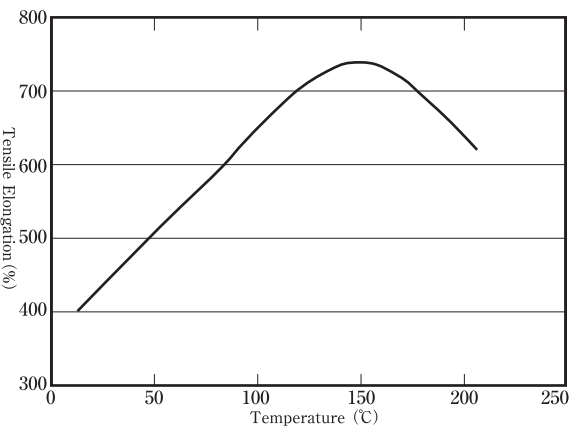


Figure 7 Effect of Temperature on Tensile Elongation

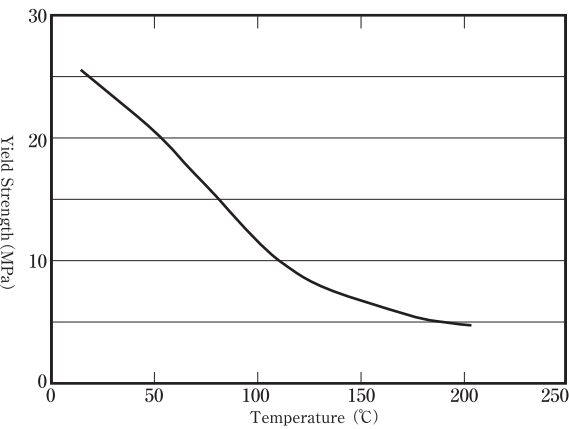


Figure 8 Effect of Temperature on Yield Strength

### C-88AP

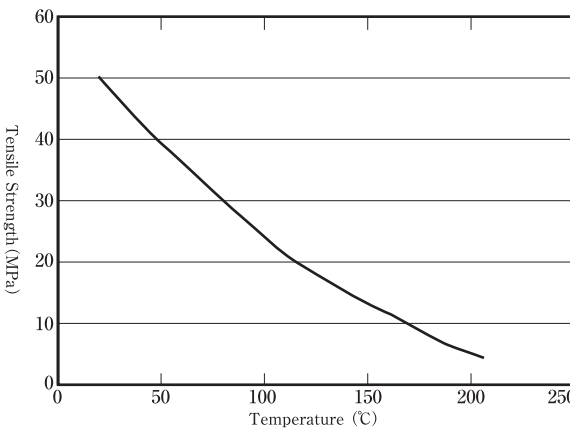


Figure 9 Effect of Temperature on Tensile Strength

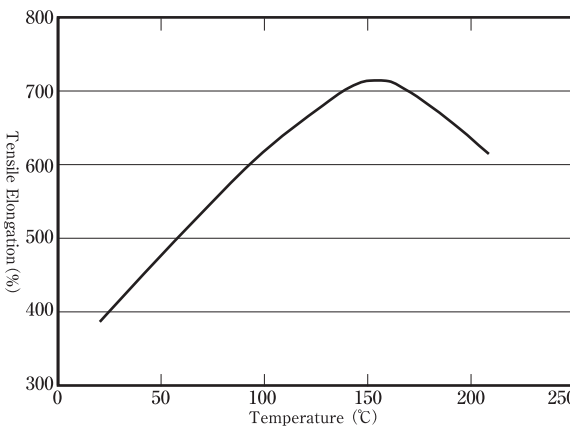


Figure 10 Effect of Temperature on Tensile Elongation

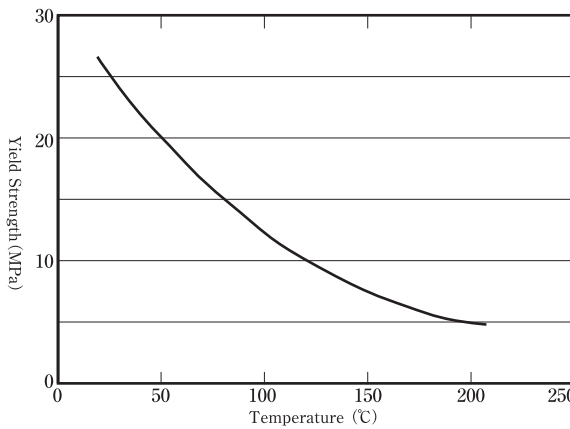


Figure 11 Effect of Temperature on Yield Strength

### C-55AXP

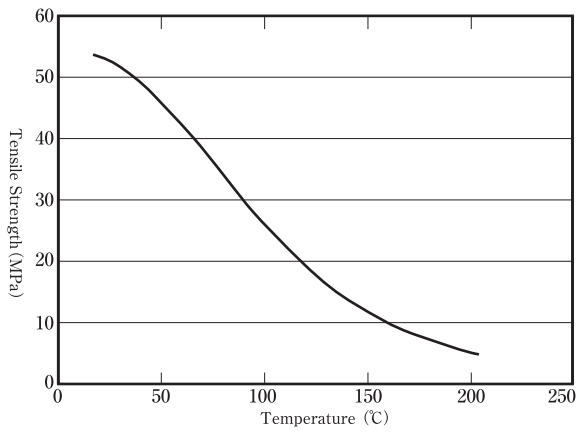


Figure 12 Effect of Temperature on Tensile Strength

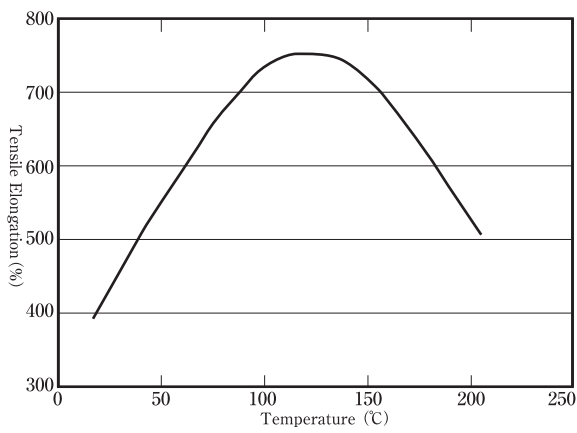


Figure 13 Effect of Temperature on Tensile Elongation

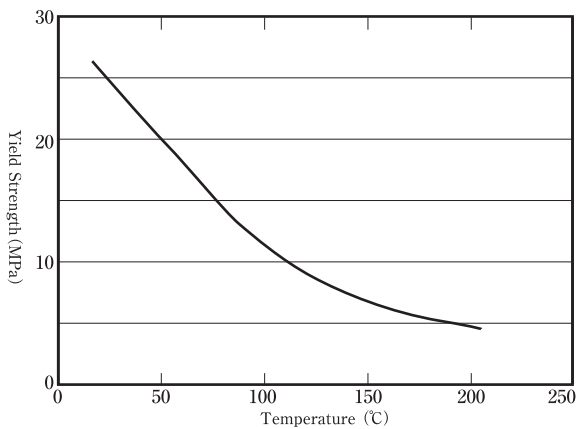


Figure 14 Effect of Temperature on Yield Strength

### C-88AXP

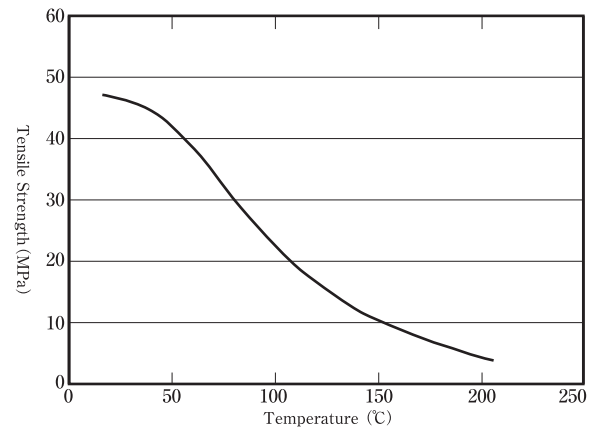


Figure 15 Effect of Temperature on Tensile Strength

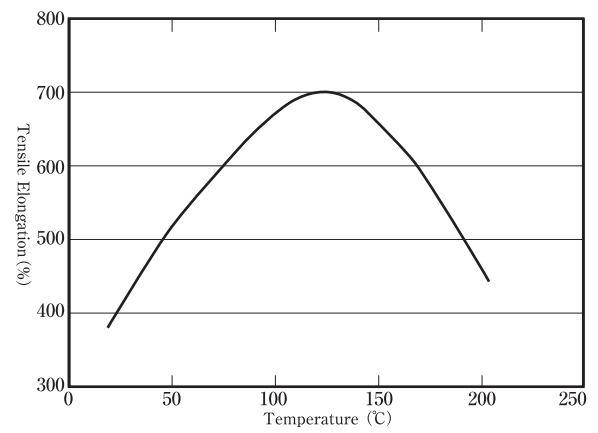


Figure 16 Effect of Temperature on Tensile Elongation

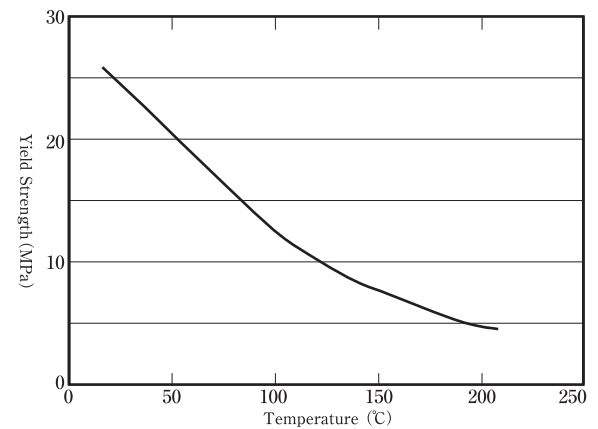


Figure 17 Effect of Temperature on Yield Strength

## C-88AXMP

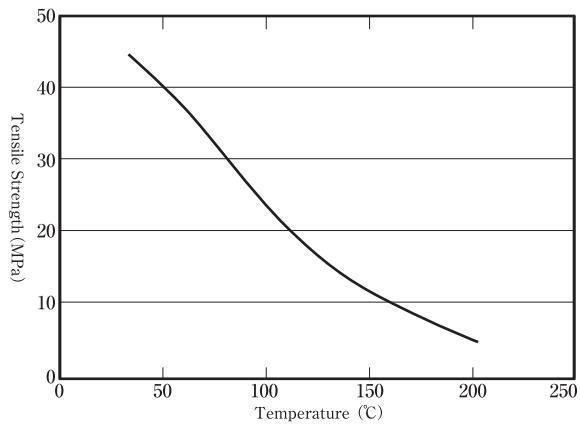


Figure 18 Effect of Temperature on Tensile Strength

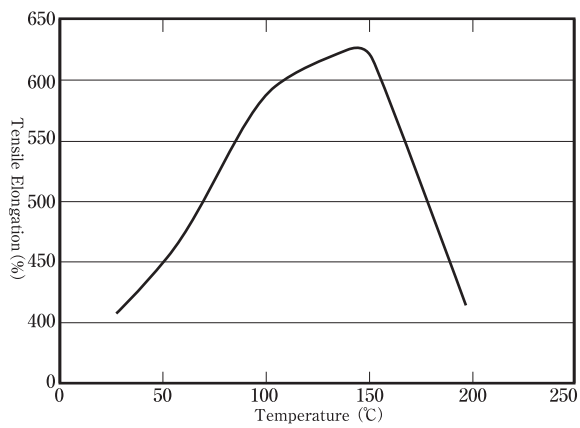


Figure 19 Effect of Temperature on Tensile Elongation

### 3-2 Tensile Creep Properties

Generally, when a constant load is applied to a plastic for a long period of time, irreversible plastic flow is caused, the amount of distortion increasing with time. This phenomenon is called creep or cold flow, and is an important property that needs to be considered when using polymers in mechanical parts etc., or in situations where the material is subjected to stress in some form. In the case of tensile creep

in Fluon®ETFE, the initial degree of distortion vary widely depending on the applied load, as shown in Figure 20, but the creep rate is very small.

Figure 21~23 show tensile creeps of various fluoropolymers. At 100°C, polyvinylidene fluoride shows a small value, but at higher temperatures, Fluon® ETFE is found to have the best values among these fluoropolymers.

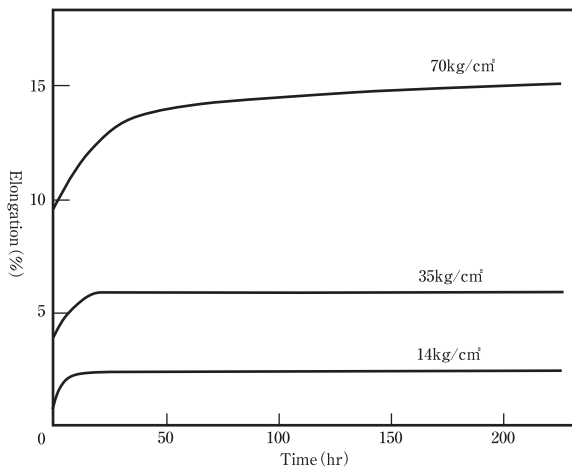


Figure 20 Tensile Creep at 100°C (ASTM D 674-56)

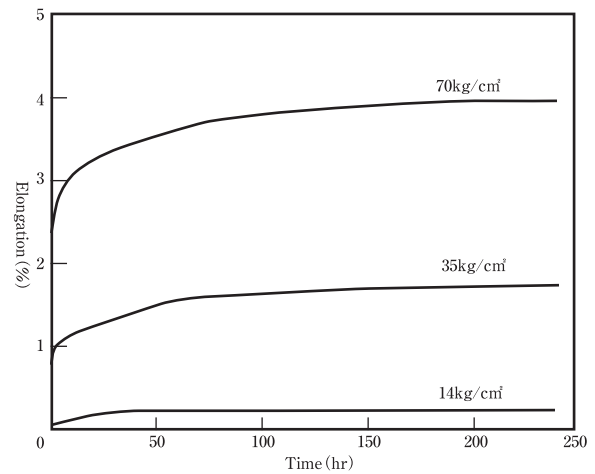


Figure 21 Tensile Creep of ETFE C-55AX (at room temp.)

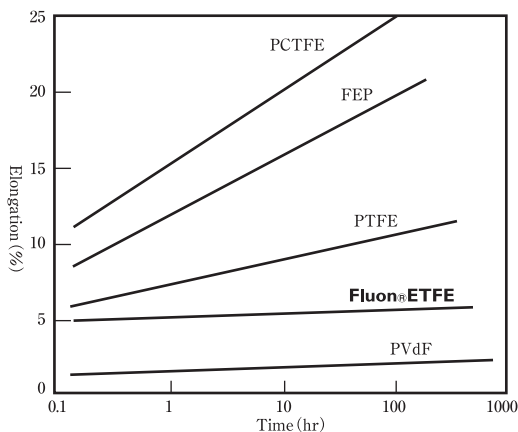


Figure 22 Tensile Creep of Various Fluoropolymers (100°C, 35kg/cm²)

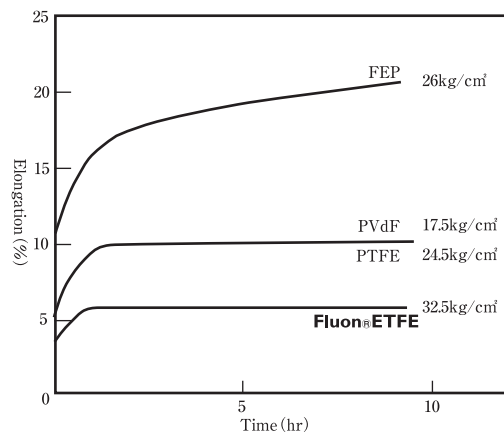


Figure 23 Tensile Creep of Various Fluoropolymers (150°C, load: 1/2 of yield strength at 150°C)

### 3-3 Compression Properties

Figure 24 shows the compression stress-strain curve of Fluon®ETFE, and Figure 25, the compression stressresidual strain curve. Also, Figures 26 and 27 illustrate the compression creep property and the compression stress relaxation property.

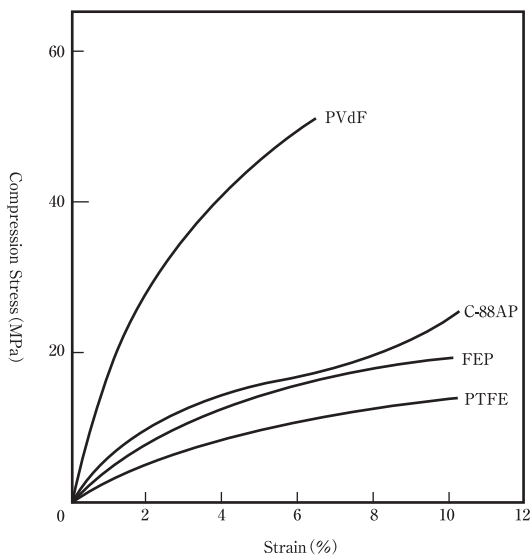


Figure 24 Compression Stress-Strain Curve

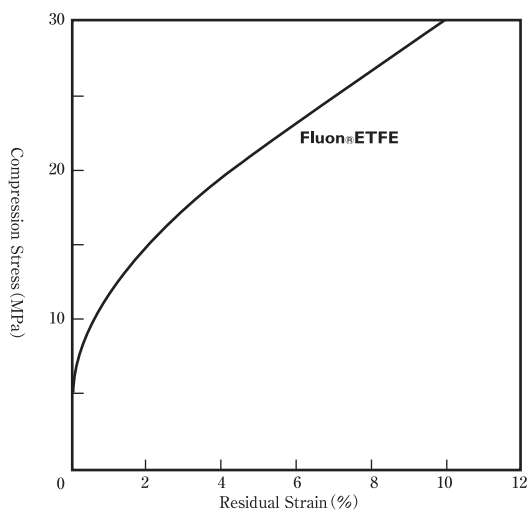


Figure 25 Compression Stress-Residual Strain Curve

(Sample: 13×13×25mm, cross head speed: F1mm/min, at room temp.)

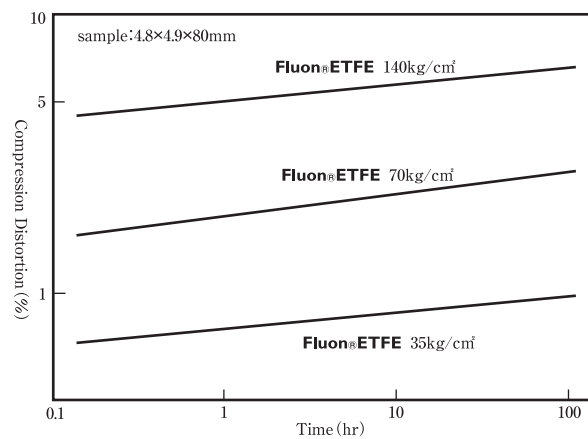


Figure 26 Dependence of Compression Creep Characteristics on Load (at room temp.)

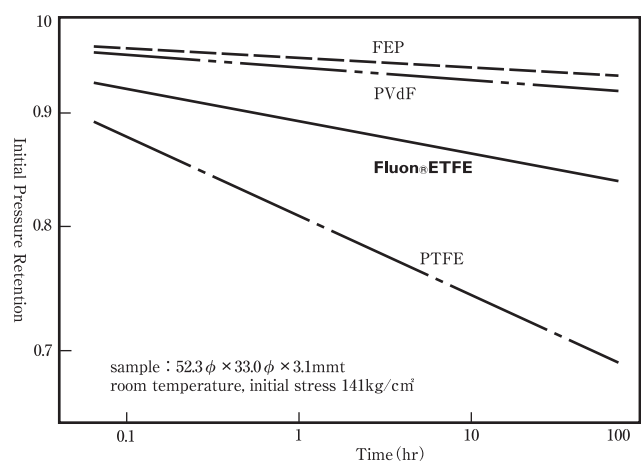


Figure 27 Compression Stress Relaxation (ASTM F38)

sample : 52.3  $\phi$  × 33.0  $\phi$  × 3.1mmt  
room temperature, initial stress 141kg/cm<sup>2</sup>

### 3-4 Flexural Properties

The effect of temperature on flexural strength and flexural modulus are shown in Figures 28~32.

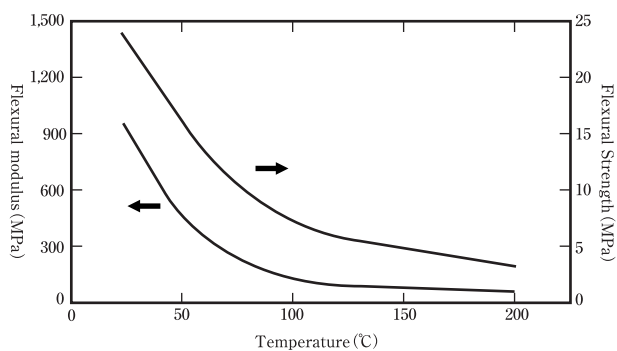


Figure 28 <Grade C-55AP>

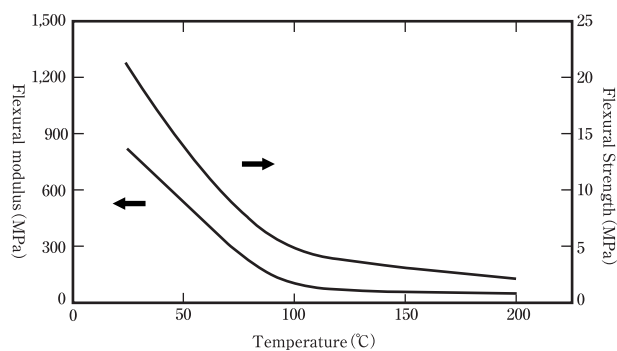


Figure 29 <Grade C-55AXP>

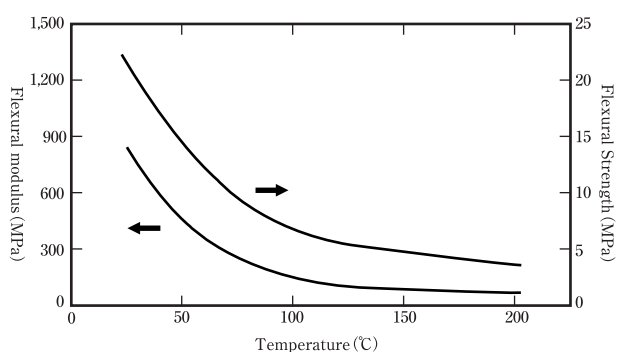


Figure 30 <Grade C-88AP>

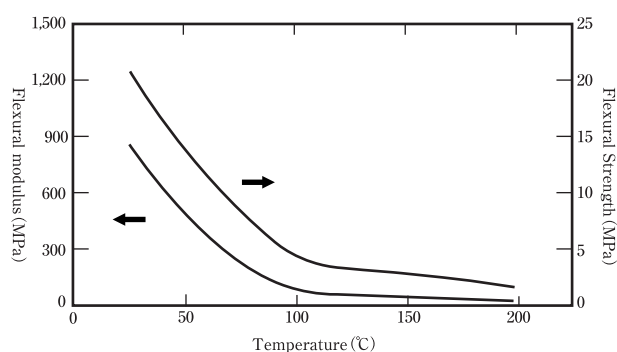


Figure 31 <Grade C-88AXP>

Test sample	injection molding (t3.2×25×80 mm)
Cross Head Speed	2 mm/min
Span	50 mm

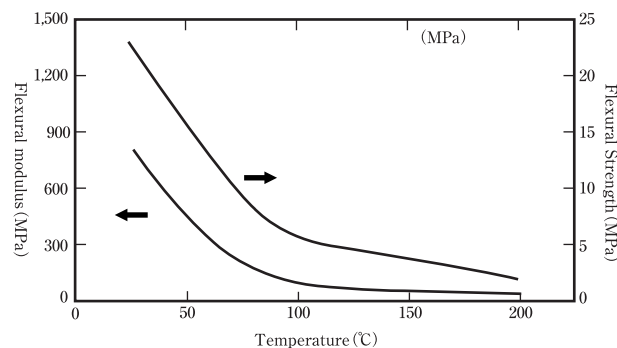


Figure 32 <Grade C-88AXMP>

### 3-5 Impact Strength

As a method of evaluating the impact strength of plastics, the Izod impact test, ASTM D256, or the Charpy impact test is used.

Fluon®ETFE has an extremely large capacity for absorbing impact energy, and maintains excellent impact resistance over a wide range of temperatures even in impact tests with a notch. Figure 34 shows the results of the Izod impact test on Fluon®ETFE and various plastics, at room temperature.

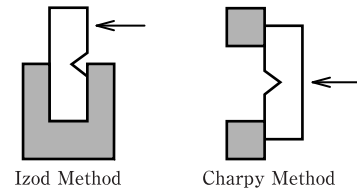


Figure 33 Methods of Testing Impact Strength

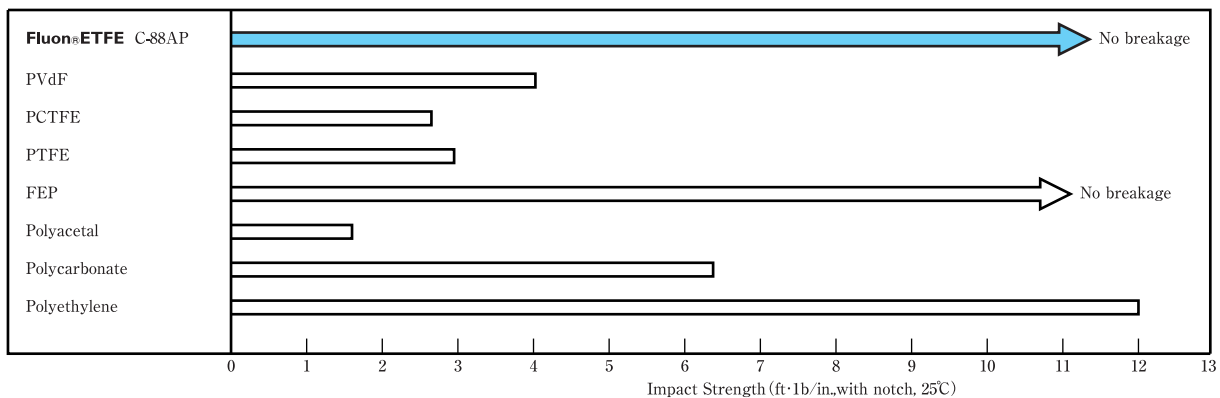


Figure 34 Izod Impact Test

Fluon®ETFE is also significantly resistant against low temperature impact, and as apparent from the results shown in Figure 35, no impact breakage occurs down to  $-80^{\circ}\text{C}$ . Destruction begins around  $-100^{\circ}\text{C}$  and the energy required for breakage in the range of  $-120^{\circ}\text{C}$  to  $-200^{\circ}\text{C}$  is about constant. The fragility point according to ASTM D746 is  $-125^{\circ}\text{C}$ , which suggests that the glass transition temperature of the noncrystalline portion of Fluon®ETFE exists around this range.

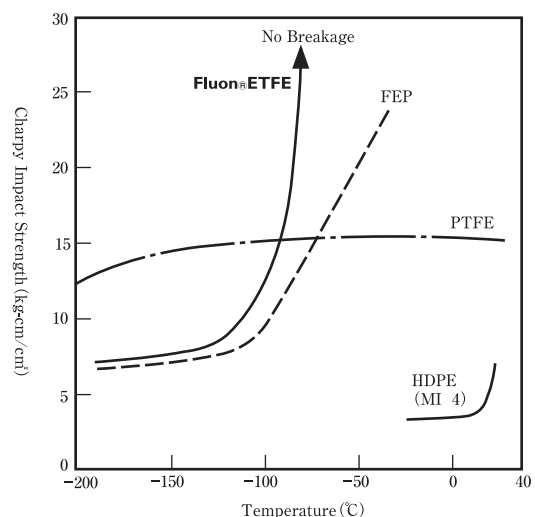


Figure 35 Effect of Temperature on Charpy Impact Strength

### 3-6 Surface Hardness


Table 7 shows the Rockwell hardness measured according to ASTM D785, represented on the R scale.

**Table 7 Surface Hardness of Various Plastics**


Plastic	Fluon®ETFE		PTFE	PFA	FEP	ECTFE	PVDF	PCTFE	PP	nylon66	polyacetal
	C-88AP	C-88AXP									
Hardness (R scale)	46	50	20	50	25	93	110	110	85~110	110	120

### 3-7 Friction and Wear Properties



The coefficients for determining the friction and wear properties vary depending on the methods and conditions chosen. Thus, it is necessary to carry out a comparative test that suits the desired application. Figures 36~41 show results obtained by the Matsubara method of friction measurement (cylindrical surface type, against SUS 316 L). The critical PV value of Fluon®ETFE is about 2.0 (kg·m/cm<sup>2</sup>·sec).

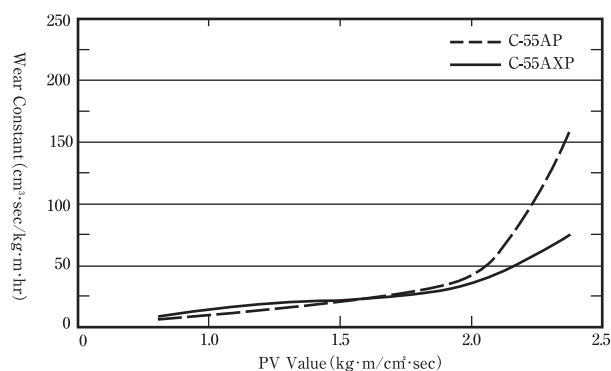


**Figure 36 C-55AP, C-55AXP Wear Constant and PV Value**

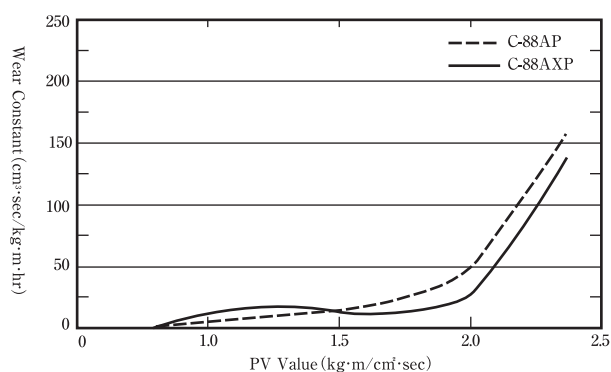

**Figure 38 C-88AP, C-88AXP Wear Constant and PV value**

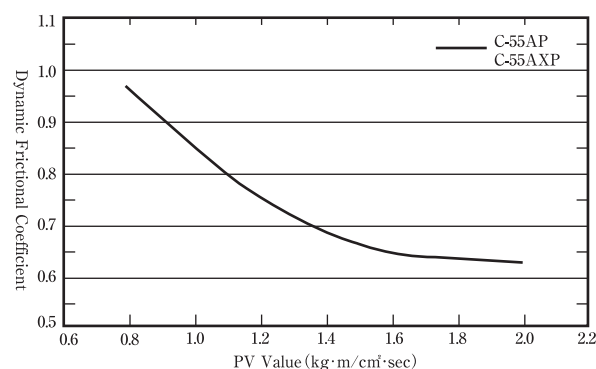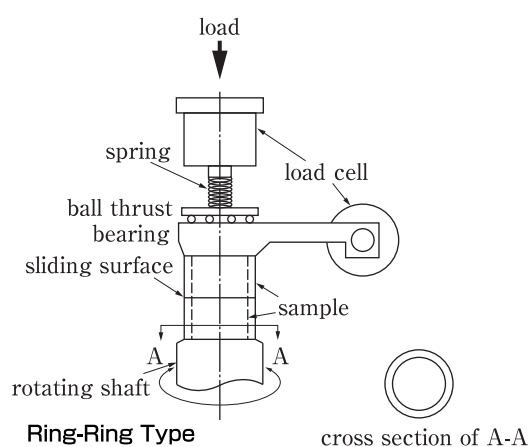

**Figure 37 C-55AP, C-55AXP Dynamic Friction Coefficient and PV Value**

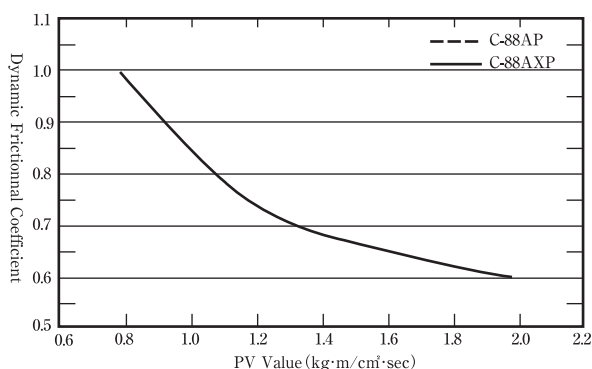

**Figure 39 C-88AP, C-88AXP Dynamic Friction Coefficient and PV Value**

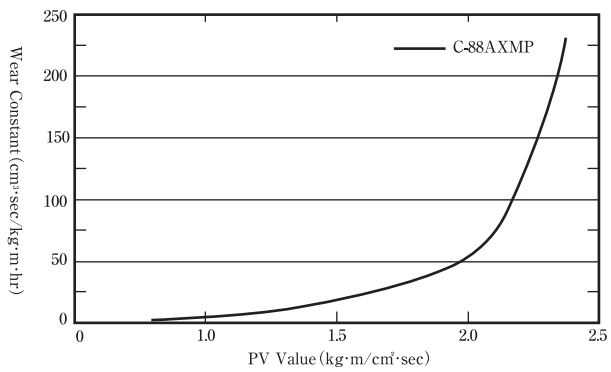


Figure 40 C-88AXMP Wear Constant and PV Value

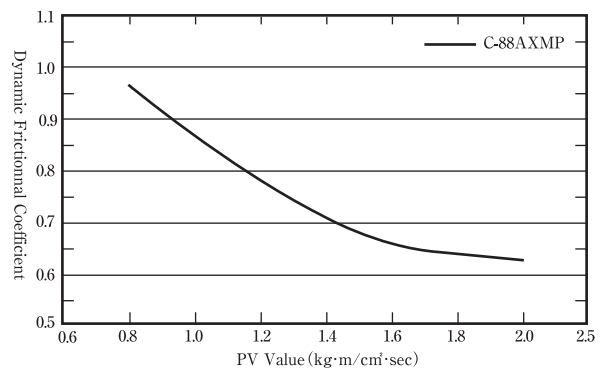


Figure 41 C-88AXMP  
Dynamic Friction Coefficient and PV value

Figures 42, 43 and Table 8 shows the dynamic friction coefficient, wear constant, and critical PV value measured by the journal-type bearing tester.

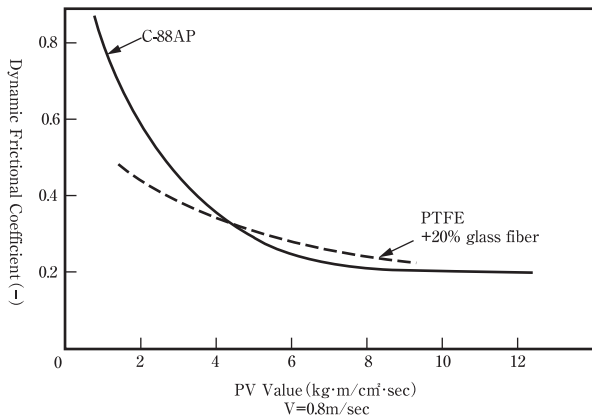


Figure 42 Dynamic Friction Coefficient and PV value

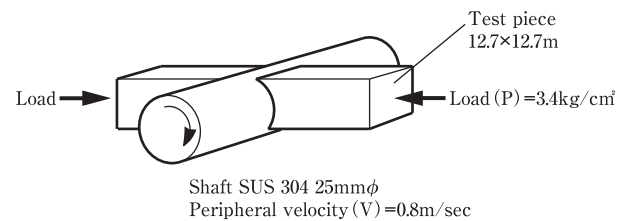


Figure 43 Journal-type bearing tester

Table 8 Abrasion Properties of **Fluon®ETFE**

		Dynamic Frictional Coefficient	Wear Constant (mm³·sec/kg·m·hr)	Critical PV value (kg·m/cm²·sec)
Fluon®ETFE	C-88AP	0.53	$145 \times 10^{-3}$	1.6
	Natural	0.28	$52 \times 10^{-3}$	1.5
	20% glass fiber	0.34	$0.1 \times 10^{-3}$	11<
	15% glaphite	0.30	$0.1 \times 10^{-3}$	11<
Nylon 66		0.50	$0.4 \times 10^{-3}$	
Polyacetal		0.32	Abnormal wear	

### 3-8 Mechanical Properties of Various Plastic

Fluon<sup>®</sup>ETFE is a polymer in which the advantages of the previous fluoropolymers are retained, while the weak aspects have been improved to obtain resilient mechanical properties. Table 9 gives the mechanical properties of various plastics.

**Table 9 Mechanical Properties of Various Plastics**

	<b>Fluon<sup>®</sup> ETFE</b>	PTFE	PFA	ECTFE	PVdF	PE	PVC (hard)	Nylon 6	Polyacetal	ASTM No.
Specific Gravity	1.73~1.75	2.1~2.2	2.1~2.2	2.15~2.17	1.76~1.77	0.92~0.96	1.3~1.4	1.10~1.14	1.42	D792
Tensile Strength (MPa)	40~54	20~39	32~39	19~22	49~60	10~44	40~70	50~80	60~70	D638
Elongation (%)	350~450	230~600	340~400	250~330	200~300	20~700	2~40	60	16	D638
Tensile Modulus (MPa)	500~800	400	—	350	800~1400	—	2500~4000	2700	3000~4500	D638
Flexural Modulus (MPa)	850~1000	400~600	530~630	670	1400~1800	500~1000	2500~2800	1000~2800	2600~2900	D790
Flexural Strength (MPa)	20~30 (yielding)	13 (yielding)	—	N0 breakage	—	11~110	70~110	56~110	100 (yielding)	D790
Compressive Modulus (MPa)	670	410	—	430	1300	—	—	—	4600	D695
Rockwell Hardness	R50~58	R18~20	R50	R25	R110	Shore D 50~70	M5~120	R100~120	R120	D785
Izod Impact Strength (ft/lb·in, with notch)	N0 breakage	3.0	N0 breakage	N0 breakage	3.5~3.8	0.5~20	0.5~20	1~3.5	1~4	D256
Frictional Coefficient (against SUS)	0.20	0.09	0.20	0.20	0.21	0.35	0.45	0.15~0.40	0.14	



## Electrical Properties of Fluon®ETFE

Among the electrical properties of polymers, the most important ones are the insulation and dielectric properties. In the high-frequency range, electrical energy is converted to thermal energy by the dielectric effect, causing the loss of electrical energy. The amount of heat generated is proportional to  $f \cdot \epsilon \cdot \tan \delta$ . Here,  $f$  represents the frequency,  $\epsilon$  is the dielectric constant, and  $\tan \delta$  is the dielectric tangent. Therefore, it is preferred that  $\epsilon \cdot \tan \delta$ , so called dielectric loss, is small.

### 4-1 Dielectric Properties

Figure 44 shows the frequency effect of the dielectric constant of some fluoropolymers. In the frequency range of  $60 \sim 10^{10}$  Hz, the dielectric constant of Fluon®ETFE is not as small as that of PTFE and FEP, but is far smaller than that of PVdF. Furthermore, in high frequencies above  $10^6$  Hz,  $\epsilon$  tends to be lower. In terms of the temperature dependence of the dielectric constant,  $\epsilon$  remains constant over a wide range.

Figure 46 shows the effect of frequency on the dielectric tangent ( $\tan \delta$ ) for Fluon®ETFE.  $\tan \delta$  in Fluon®ETFE has a maximum value close to  $10^8$  Hz. Figure 47 shows the temperature dependence of the dielectric tangent. Curves are different depends on frequency.

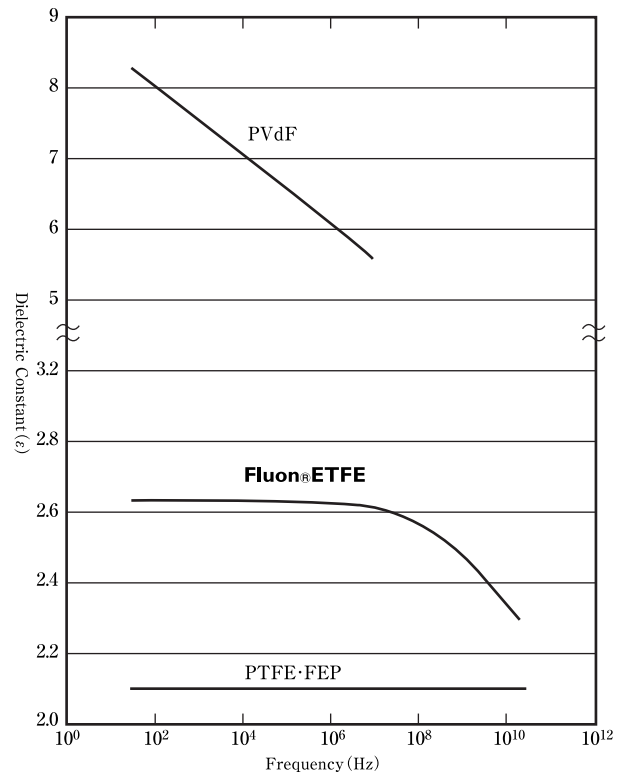


Figure 44 Effect of Frequency on Dielectric Constant (25°C)

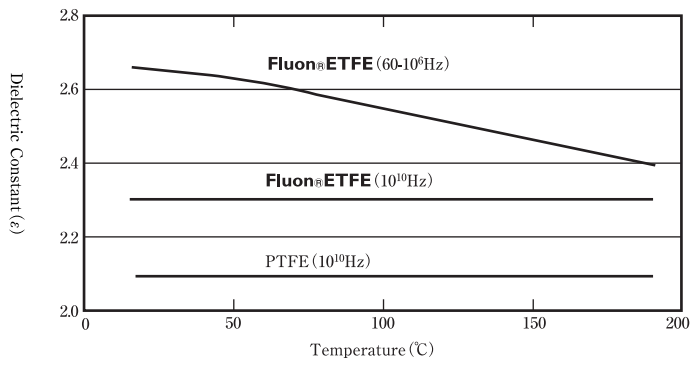


Figure 45 Effect of Temperature on Dielectric Constant

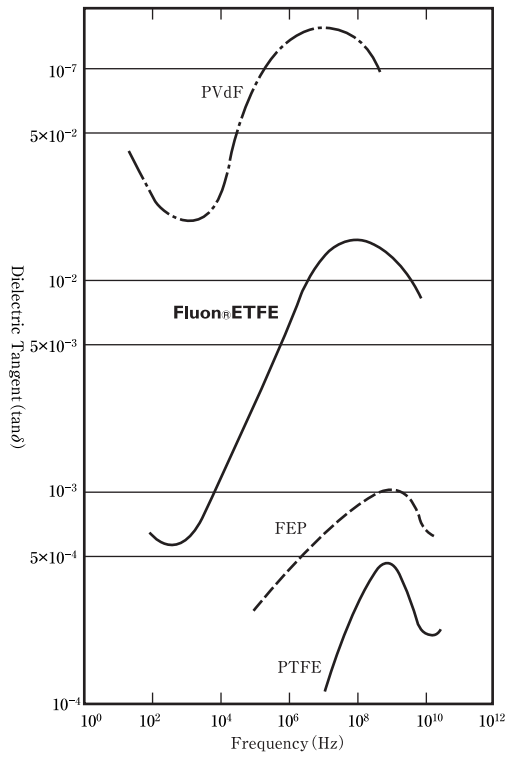


Figure 46 Effect of Frequency on Dielectric Tangent (25°C)

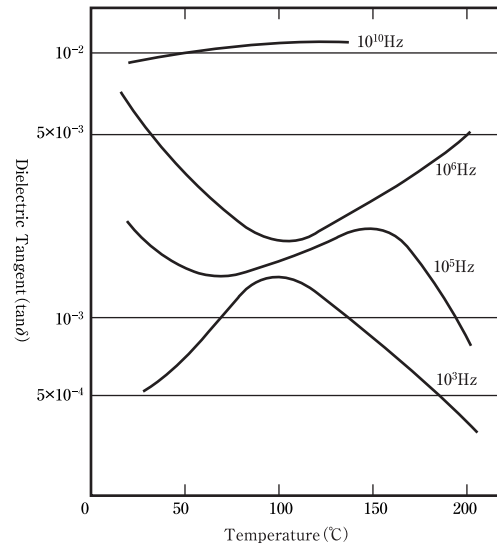


Figure 47 Effect of Temperature on Dielectric Tangent

## 4-2 Insulation

The insulation resistance is generally represented by the volume specific resistance, which indicates the degree by which the polymer, as an insulator, resists the flow of electric current through itself. The larger this value, the better the polymer is as an insulator. With respect to the insulation break-down voltage, another important characteristic of insulation materials, Fluon®ETFE proves to be an excellent material. The insulation break-down voltage depends on the thickness of the sample.

Figure 50 shows the results of the effect of film thickness on the break-down voltage, and indicates that the break-down voltage is proportional to 0.65 power of the thickness up to 100  $\mu\text{m}$ .

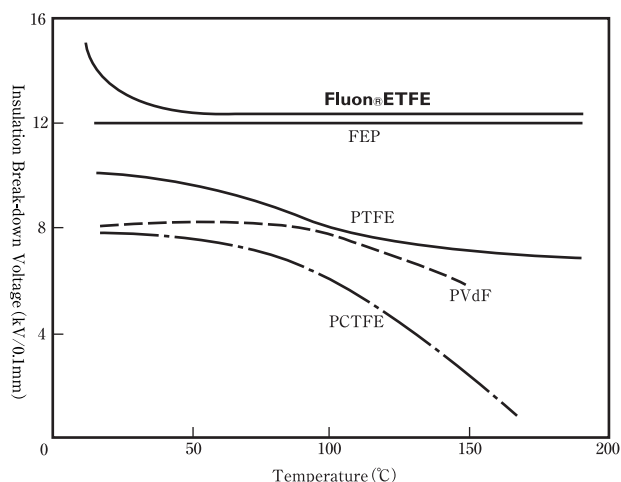


Figure 49 Temperature Dependence of Insulation Break-down Voltage

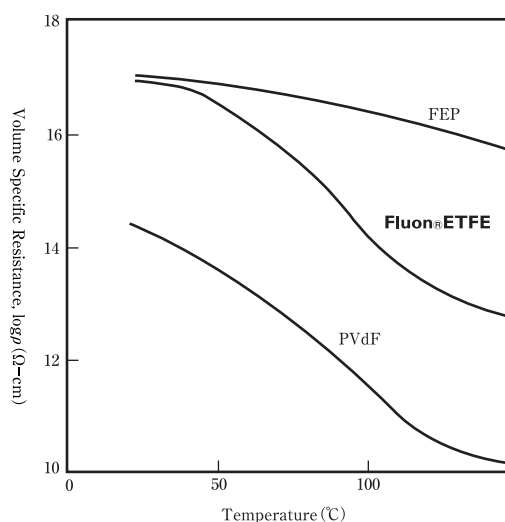


Figure 48 Temperature Dependence of Volume Specific Resistance

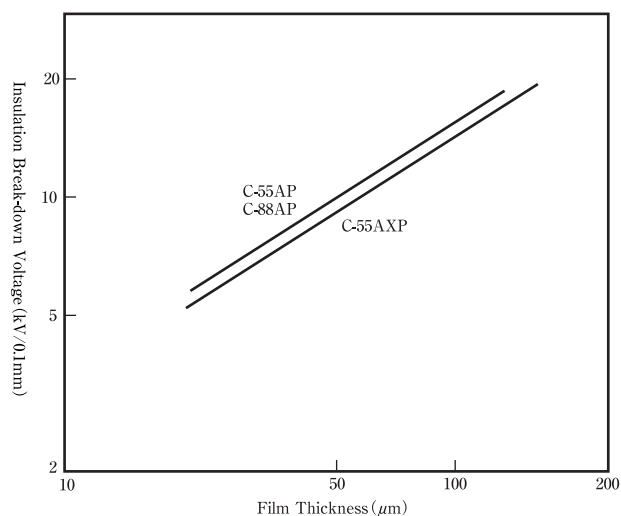


Figure 50 Dependence of Insulation break-down Voltage on Sample Thickness (room temperature)

## 4-3 Arc Resistance

The arc resistance of Fluon®ETFE measured according to ASTM D495 is 120 seconds. It has been reported to be 300 seconds or higher for PTFE and 170 seconds or higher for FEP. This high value is said to be due to the fact that the polymer decomposed by the arc is dispersed in the form of low-molecular-weight fluoro-carbon, and conductive materials such as carbon do not remain in the polymer.

## 4-4 Tracking Resistance

As a result of scintillation caused by the presence of electrolyte on the surface, the surface of the polymer is carbonized, forming a track, and becomes conductive.

This phenomenon is called tracking, and the resistance to it is known as tracking resistance, which represents an electric insulation property under special conditions.

The measurement method used here, is the electrolyte dropping method, defined by IEC. Table

10 shows the results obtained.

In the table, the comparative tracking index is the voltage at which 50 drops cause tracking formation in the range of 0~600 V. If no destruction is observed with 600 V and 50 drops, the maximum depth (mm) of the tracking groove formed on the surface after dropping the 51st drop is measured and shown in ( ).

Fluon®ETFE is among the conventional polymers having the best tracking resistance.

Table 10 Tracking resistance

	Fluon®ETFE	PTFE	FEP	PCTF	Polyethylene	Polystyrene
Tracking Index (V)	(0)	(0)	(0)	(0)	310	540

## 4-5 Cut-through Resistance

Cut-through resistance is one method to evaluate electrical properties of materials used for wire coating.

The cut-through resistance is obtained as the maximum load at which the insulation is maintained, when the covered wire is placed on a sharp edge and put under a load.




Figure 51 Method of Testing Cut-through Resistance

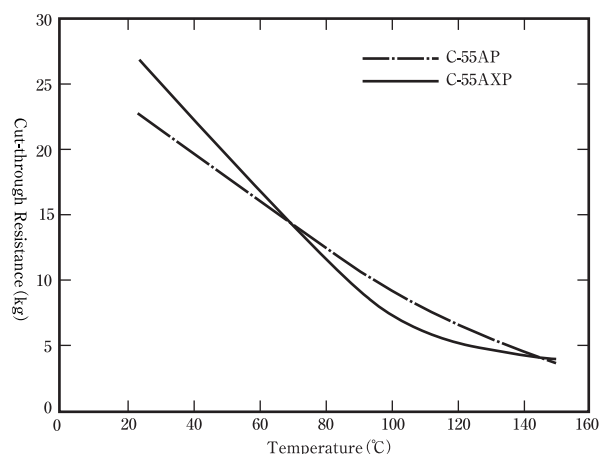


Figure 52 Effect of Temperature on Cut-through Resistance

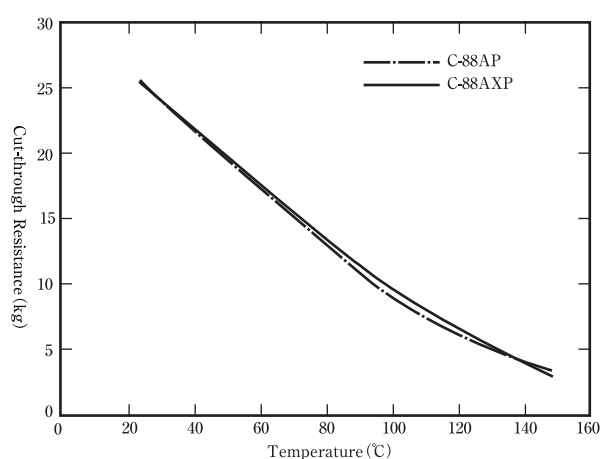


Figure 53 Effect of Temperature on Cut-through Resistance



## Chemical Properties of Fluon®ETFE

### 5-1 Chemical Resistance

Fluon®ETFE is stable against most chemicals and has excellent chemical resistance. Table 11 shows the effect of various chemicals on Fluon®ETFE. Other than being affected, to a certain degree, by strong oxidizing acids such as concentrated nitric acid, etc., organic amines, and sulfonic acid, at high temperature, Fluon®ETFE shows excellent chemical resistance to other inorganic acids and bases and organic solvents.

Table 11 shows the results obtained by using micro-dumbbells of 1mm thickness. Property changes less than 15% should be no problem for usage.

**Table 11 Chemical Resistance of Fluon®ETFE**

Chemical Categories	Chemical		Temp.(°C)	Days	Retention (%)	
					Elong.	Wt. Gain
Inorganic acids	Conc. Hydrochloric acid	35%	100	10	100	0.0
	Sulfuric acid	78%	121	10	100	0.1
		98%	121	10	100	0.0
	Oleum		25	10	96	1.3
	Nitric acid	25%	100	14	100	—
		60%	120	10	100	0.7
		70%	60	60	100	—
		70%	120	7	10	—
	Fuming nitric acid		25	10	92	0.6
	Hydrofluoric acid		25	7	95	0.1
Alkalis	Sodium hydroxide	10%	120	10	97	0.0
		50%	120	10	100	—0.3
	Potassium	20%	100	7	100	0.0
	Ammonium hydroxide	15%	66	7	98	0.1
Other Inorganic Compounds	Chlorine		90	10	94	—
			120	7	85	7.0
			150	10	41	—
	Bromine		60	7	100	0.1
	Hydrogen peroxide		25	7	98	0.0
	Water		100	7	100	0.0
	Phosphorus trichloride		75	7	99	—
	Phosphorus oxychloride		100	7	99	—
	Silicon tetrachloride		55	7	100	—
	Sulfuric chloride		70	7	100	6.0
	Carbon disulfide		100	30	98	1.0
	Ferric chloride	25%	70	7	100	6.0

Chemical Categories	Chemical	Temp. (°C)	Days	Retention (%)	
				Elong.	Wt. Gain
Amines	Aniline	25	11	98	0.1
		120	30	82	1.6
	N-methylaniline	120	30	100	0.0
	N-butylamine	78	7	93	5.0
	N-dibutylamine	120	30	99	0.0
		159	7	72	–
	N-tributylamine	120	30	95	–
	Pyridine	116	11	100	3.8
	Ethylenediamine	25	11	100	–
		117	11	96	2.0
	Triethylamine	90	11	90	1.5
	Dimethylformamid	25	11	100	0.4
		120	11	95	2.7
	Dimethylacetamide	121	7	98	3.6
Aromatic compounds	Phenol	100	11	100	0.3
		120	11	67	0.9
	Benzaldehyde	120	11	94	2.3
		120	11	98	3.6
	Chlorobenzene	25	11	87	0.4
		120	11	98	3.6
	Nitrobenzene	25	11	98	0.2
		120	11	96	3.0
	Benzene	80	11	95	2.6
Chlorine compounds	Toluene	111	11	100	2.6
		120	11	88	2.5
	Cresol	120	11	80	1.7
	Chloroform	25	11	100	1.6
		61	11	80	1.7
	Carbon disulfide	25	11	100	0.1
		77	11	80	5.0
	Methylene chloride	40	11	100	3.9
	Trichloroethylene	87	11	100	4.8
	Perchloroethylene	77	11	100	5.5
	Ethylene dichloride	84	11	88	3.8
	Freon 113	47	11	–	3.8
Ethers	Epichlorohydrin	117	11	78	3.7
	Benzoyl chloride	120	30	100	0.0
	Propylene oxide	25	11	82	3.2
		25	11	98	2.3
	Tetrahydrofuran	66	11	92	4.2
		105	11	86	6.0
	Ethylether	25	11	87	1.0
	Cellosolve	121	11	88	1.3

Chemical Categories	Chemical	Temp. (°C)	Days	Retention (%)	
				Elong.	Wt. Gain
Ketones	Acetone	25	11	97	2.3
		56	11	93	2.5
	Methylethylketone	25	11	100	1.6
		80	11	100	3.1
	Methylisobutylketone	25	11	–	0.3
		116	11	100	3.3
Organic acid	Acetophenone	121	11	80	2.5
	Cyclohexanone	121	11	72	5.2
	Glacial acetic acid	25	11	87	0.7
		118	11	80	2.2
	Oxalic acid	120	11	100	0.1
	Citric acids	120	11	87	0.1
	Stearic acid	120	11	83	0.1
	Formic acid	100	11	100	0.1
	Glycolic acid	120	11	98	0.0
	Chloroacetic acid	100	11	100	0.6
	Trichloroacetic acid	100	11	84	2.5
	Phthalic acid	120	11	100	0.1
Ester	Ethyl acetate	25	11	100	2.3
		77	11	100	3.4
	Butyl acetate	120	11	88	3.5
	Dimethyl phthalate	25	11	87	0.4
Alcohols	Methanol	65	11	93	0.3
	Ethanol	78	11	98	0.6
	Cyclohexanol	120	11	88	1.2
	Benzyl alcohol	120	11	92	0.8
	Propyl alcohol	97	11	93	0.7
	Diacetone alcohol	120	11	91	2.8
Other hydrocarbones	Hexane	69	11	84	1.1
	Skidroll 500B	120	11	100	0.6
	Mineral oil ASTM No.3	120	11	96	0.2
	Octane	120	11	98	0.2
	Octene	120	11	99	1.1
	Cyclohexane	81	11	94	1.4
	Decalin	120	7	95	–
	Dimethylsufoxide	120	11	89	1.3
	Acetonitrile	82	11	93	1.5

## 5-2 Chemical Stress Crack

Some polymer materials form cracks when placed under stress in chemicals over a long period of time. Table 12 shows the results of testing method ASTM D 1693, where a narrow strip of plastic sheet, 2.3 mm thick and 38 mm long, was bent 180° and soaked in chemicals for 10 days. The sheet was then examined for crack formation. The results obtained show that Fluon®ETFE has good adaptability in chemical stress.

**Table 12 Chemical Stress Crack of Fluon®ETFE**

Chemical	Temperature (°C)	Number of cracked pieces (cracked/tested)		
		C-55AP	C-88AP	C-55AXP
Nitrobenzene	121	0/3	0/3	0/3
Aniline	121	0/3	0/3	0/3
Benzaldehyde	121	0/3	0/3	0/3
Chlorobenzene	121	0/5	0/3	0/3
Ethylenediamine	117	0/5	0/3	0/3
Dimethylformamide	121	0/5	0/3	0/3
Dimethylsulfoxide	121	0/3	0/3	0/3
Dimethylacetamide	121	0/3	0/3	0/3
Nitric acid 60%	121	0/3	0/3	0/3

## 5-3 Weatherability

Fluon®ETFE shows good weatherability, and "Fluon®ETFE Film", a film obtained by extrusion molding, will not change in properties even when used outdoors as a coating material.

**Table 13 Weatherability of Fluon®ETFE Film**

Characteristics	Film Grade Exposure Time (hrs)	12μm thickness			16μm thickness (gray)		
		0	1000	2000	0	1000	2000
Tensile Strength	MPa	48	49	49	47	47	47
Tensile Retention	%	—	(102)	(102)	—	(100)	(100)
Elongation (breakage)	%	340	395	390	330	335	330
Modulus Retention	%	—	(116)	(115)	—	(101)	(100)
Tensile Moduluskg	MPa	780	820	820	780	760	760
Modulus Retention	%	—	(105)	(105)	—	(97)	(97)

Measurement method : JIS D205-1970 Sunshine-Weather-O-Meter

---

## 5-4 Hot Water Resistance

---

The water absorption of Fluon®ETFE was measured according to test methods ASTM D570, where a sheet, 6 mm in thickness, is soaked in boiling water for 2 hours. The results obtained are shown in Table 14. The water absorption is found to be extremely small, thus, indicating that the electrical and mechanical properties are not affected by the presence of moisture.

Table 15 shows the change in strength of Fluon®ETFE, measured at room temperature after soaking a 1mm thick sheet in boiling water for a given amount of time.

As the chemical resistance data suggests, Fluon®ETFE shows excellent resistance to hot water, too.

**Table 14 Water Absorption of Fluon®ETFE**

<b>Fluon®ETFE</b>	Water Absorption (wt%)
C-55AP C-88AP	less than 0.03

**Table 15 Boiling Water Resistance**

Grade	Property	Characteristics After Soaking		
		0 HR	260 HR	2000 HR
C-55AP C-88AP	Tensile Strength (MPa)	44	43	43
	(retention %)		(99)	(98)
	Elongation (%)	430	405	480
	(retention %)		(94)	(113)

## 5-5 Gas Permeation and Moisture Permeation

The permeation of oxygen, nitrogen, carbon dioxide, etc., are approximately constant regardless of film thickness. The activation energy is 6~8 kcal/mol.

The gas permeation and moisture permeation of Fluon®ETFE are similar to those of polyethylene or polypropylene. Gas permeability was obtained by ASTM D1434, moisture permeability by the cup method of ASTM E96, and shown in Tables 16 and 17.

Table 16 Gas Permeation

Gas Permeability temperature : 23°C unit : $10^{-11}\text{cm}^3(\text{STP}) \cdot \text{cm}/\text{sec} \cdot \text{cm}^2 \cdot \text{cmHg}$		
	C-55AP	C-55AXP
Oxygen	6.1	8.9
Nitrogen	2.3	3.0
Helium	63	86
Carbon dioxide	25	46
Methane	0.8	—

Table 17 Moisture Permeation

temperature : 23°C 0-90RH% unit : $\text{g}/\text{m}^2 \cdot 24\text{hrs} \cdot 0.1\text{mm}$	
Grade	Moisture Permeability
C-55AP, 88AP	1.3

## 5-6 Light Transmittance

The refractive index of Fluon®ETFE is 1.40, which is smaller than that of conventional plastics.

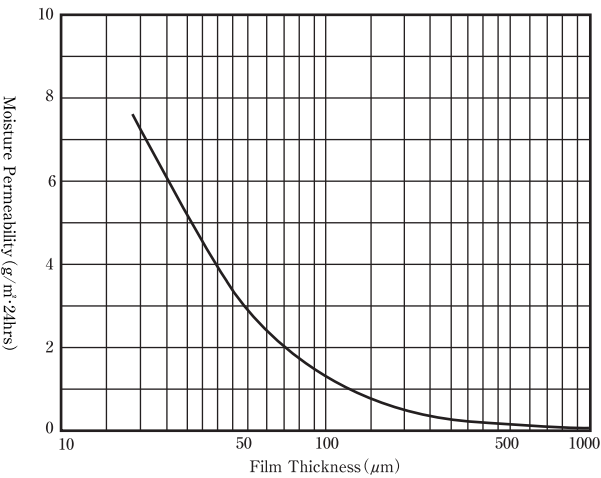


Figure 54 Effect of Film Thickness on Moisture Permeability (23°C, 0-90RH%) ASTM E96

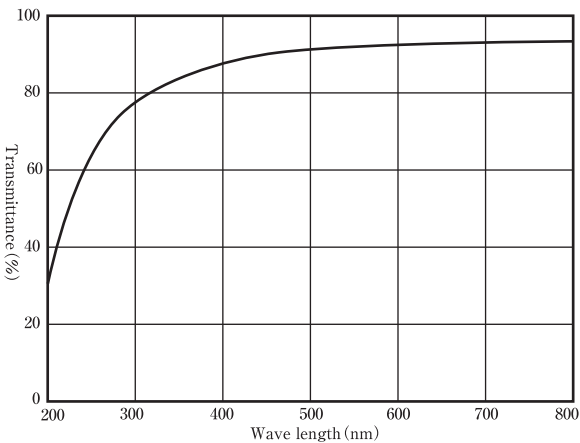


Figure 55 Light transmittance (C55AXP, 50μm)

## 5-7 Radiation Resistance

Fluon®ETFE shows radiation resistance significantly higher than that of polytetrafluoroethylene, but as a result of irradiation, cross linking and decomposition occur concurrently, and consequently, mechanical properties are reduced as shown in Figures 56~63.

The irradiation dose rate is  $1 \times 10^6$  rad/hr.

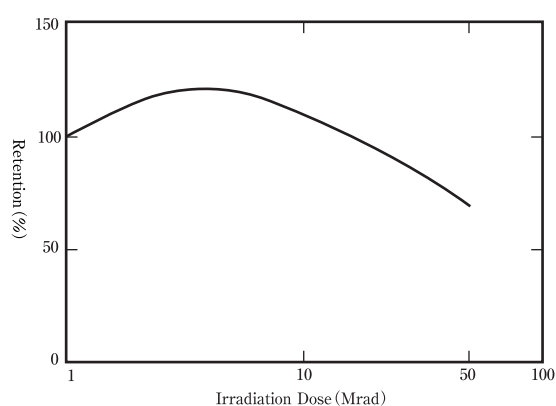


Figure 56 Change in Tensile Strength <C-55AP>

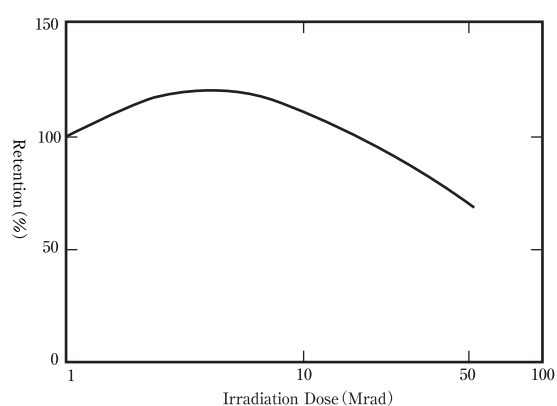


Figure 57 Change in Tensile Elongation <C-55AP>

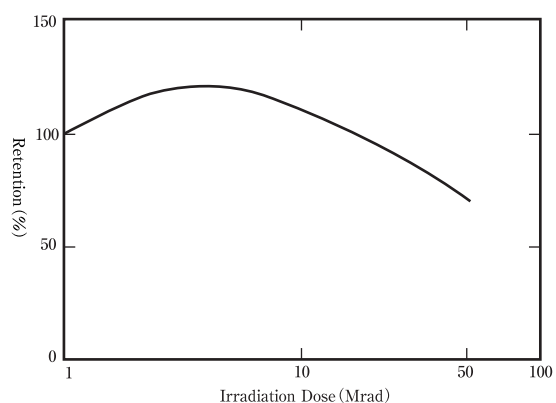


Figure 58 Change in Tensile Strength <C-88AP>

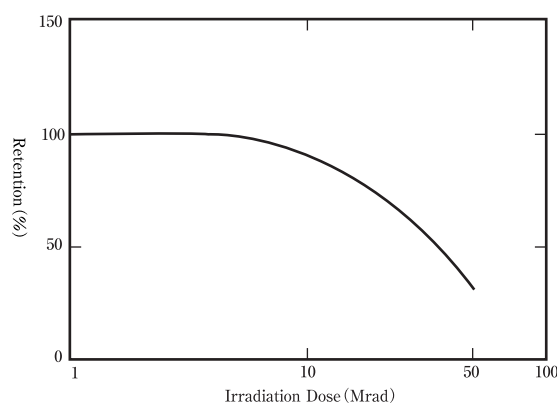


Figure 59 Change in Tensile Elongation <C-88AP>

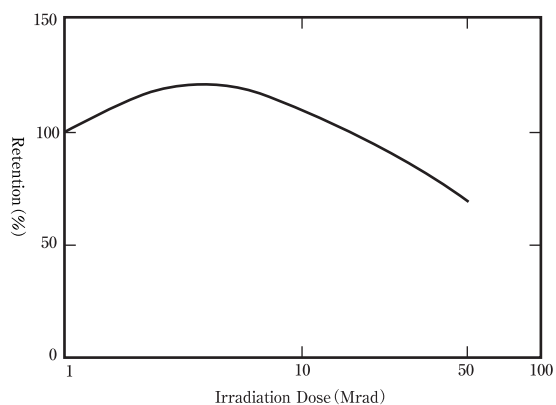


Figure 60 Change in Tensile Strength <C-55AXP>

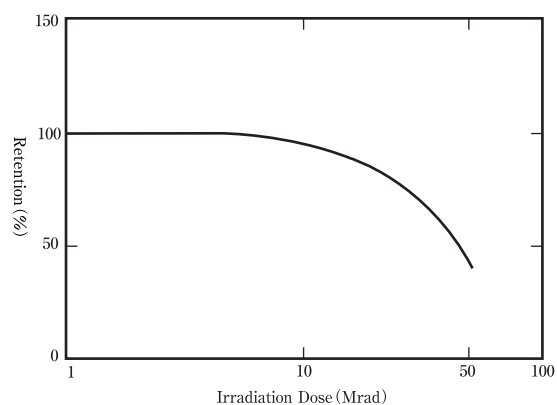


Figure 61 Change in Tensile Elongation <C-55AXP>

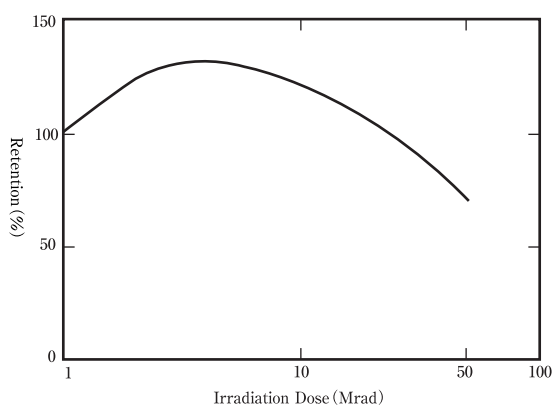


Figure 62 Change in Tensile Strength (C-88AXP)

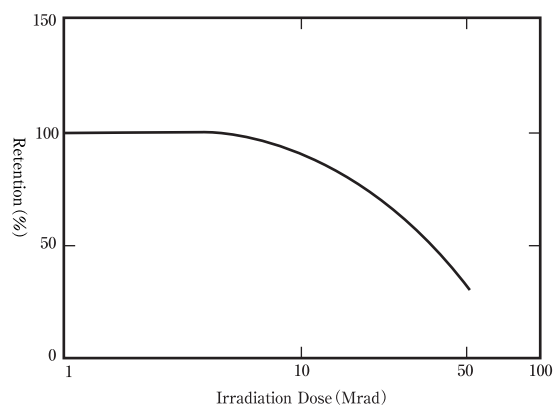


Figure 63 Change in Tensile Elongation (C-88AXP)

## 5-8 Food Safety

Fluon®ETFE is thermally and chemically stable. Furthermore, no plasticizer is added, and as a result, is safe with respect to food hygiene.

### (1) Test according to the Ministry of Health, Labour and Welfare Notification No.20, No.370, and No.434

Results of tests carried out by the Chemical Product Testing Association show that the resin satisfy the requirements, with respect to potassium permanganate consumption, evaporation residue, heavy metal, formaldehyde, and phenol.

### (2) Acute Toxicity Test (LD50)

The acute toxicity test carried out by the Department of Public Health, Faculty of Medicine, Nihon University, revealed no toxicity.

### (3) Food Hygiene Test in USA

The results of toxicity and extraction tests carried out by D and R Testing Institute (Spencer-ville, Ohio, USA), according to the guidelines of the US FDA, showed the safety factor to be extremely high.



## Fluon®ETFE

### Physical Properties

Tables 18~19 outlines the basic physical properties of Fluon®ETFE.

**Table 18 Basic Physical Properties of Fluon®ETFE**

Test	ASTM	Unit	C-55AP	C-55AXP	C-88AP	C-88AXP	C-88AXMP
Melt Flow Rate	D-3159	g/10min	3.9~6.5	3.9~6.5	9.0~12.0	9.0~12.0	27~43
Specific Gravity	D-792	—	1.74	1.73	1.74	1.73	1.73
Melting Point	—	°C	265	258	267	260	260
		°F	509	496	513	500	500
Tensile Strength	D-638	MPa	52	52	48	48	42
		Psi	7,500	7,500	7,000	7,000	6,100
Tensile Elongation	D-638	%	382	414	415	415	433
Flexural Modulus	D-790	MPa	960	930	910	890	870
		Psi	139,000	135,000	132,000	129,000	126,000
Flexural Strength	D-790	MPa	26	25	25	25	24
		Psi	3,800	3,600	3,600	3,600	3,500
Durometer D scale	D-785	—	67	67	67	67	67
Izod Impact Strength	D-256 (notched)	J/m	non break	non break	non break	non break	non break
Linear Thermal Expansion Coefficient	D-696	10 <sup>-5</sup> /°C	9.3	9.3	9.4	9.4	9.4
Oxygen Index	D-2863	%	32	32	32	32	32
Chemical Resistance	—	—	excellent	excellent	excellent	excellent	excellent
Dielectric Constant (10 <sup>2</sup> ~10 <sup>6</sup> Hz)	D-150	—	2.6	2.6	2.6	2.6	2.6
Molding Shrinkage (flow direction)	—	%	1.8	1.8	1.8	1.8	1.8



## Molding of Fluon®ETFE

Unlike polytetrafluoroethylene, a typical fluoropolymer, Fluon®ETFE can be processed by conventional melt processes. Specifically, its melt viscosity at molding temperature is  $10^3 \sim 10^5$  poise, which is about the same as that of conventional thermoplastics, and as a result, methods such as injection, extrusion, blow molding, and powder coating, can be used.

### 7-1 Raw Resin and its Handling

The grades of Fluon®ETFE have been described in Chapter 1 ; C-55 is suitable for heavy-gage molding, and C-88 for light-gage molding. Since Fluon®ETFE is not hygroscopic, no preliminary drying of the raw resin is necessary. However, during storage, it is preferable to have the container sealed tightly, so that no moisture is absorbed and the resin is not contaminated by dust due to static electricity.

Fluon®ETFE is a thermally stable resin, but if subjected to temperature above  $350^\circ\text{C}$ , thermal decomposition is induced. Thus, the resin cannot be kept at high temperatures for long periods of time. It is preferable not to leave the resin in a molding machine for more than 30 minutes when interrupting the operation. In such situations, it is suggested that the temperature of the molding machine be lowered.

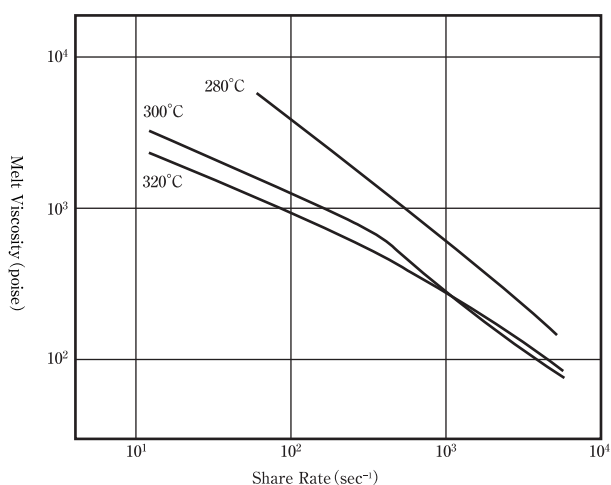


Figure 64 Effect of Shear Rate on Melt Viscosity <C-55AP>



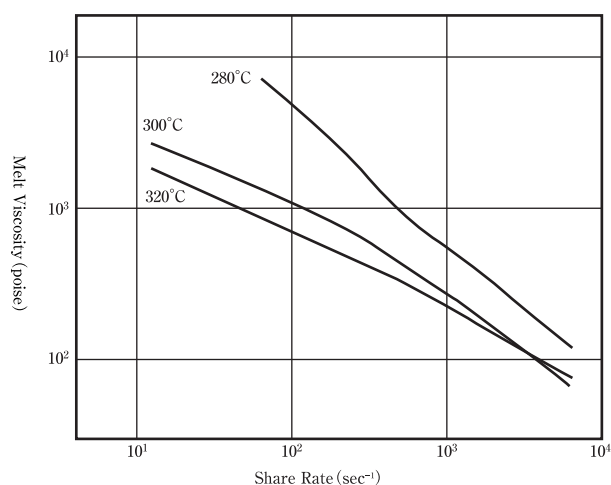



Figure 65 Effect of Shear Rate on Melt Viscosity <C-88AP>

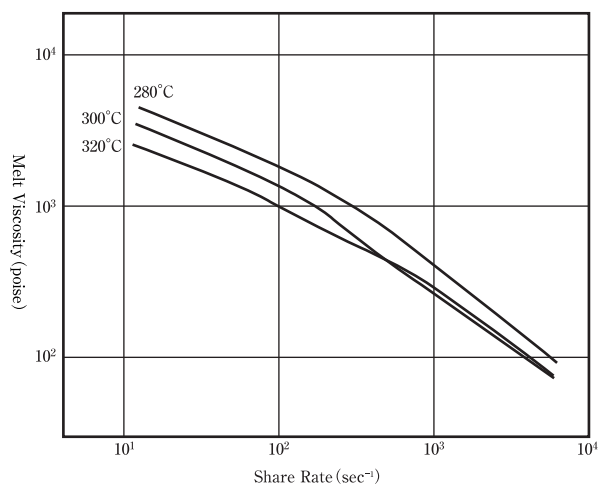

**Figure 66 Effect of Share Rate on Melt Viscosity <C-55AXP>**

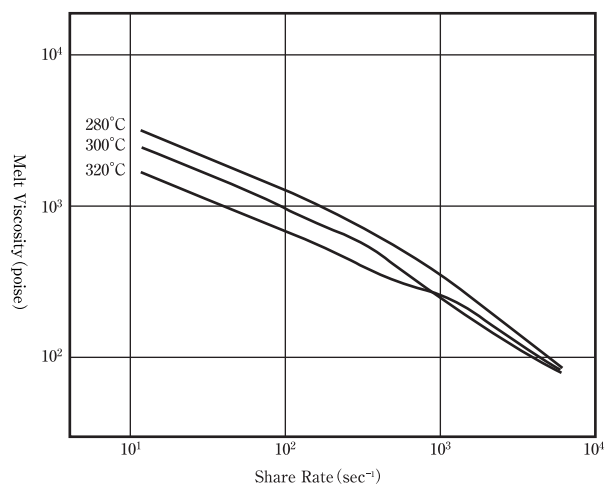

**Figure 67 Effect of Share Rate on Melt Viscosity <C-88AXP>**

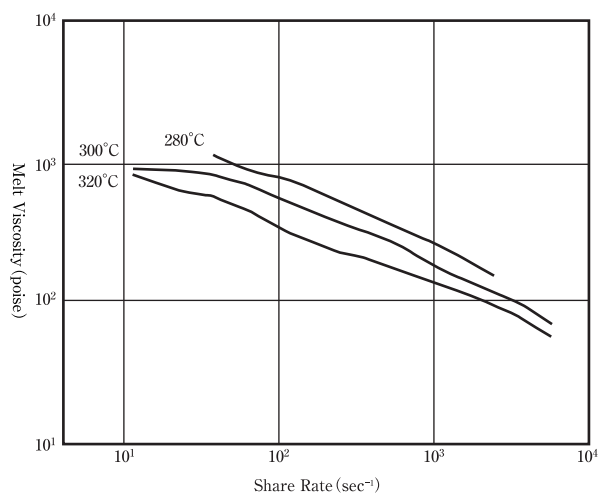

**Figure 68 Effect of Share Rate on Melt Viscosity <C-88AXMP>**

---

## 7-2 Injection Molding

---

### (1) Injection Machine and Molding Material

Any of the plunger-type and screw-in-line-type injection machines may be used for molding, as long as the heater holds a heat capacity of up to 340°C. The material of the molding machine, corrosion resistant materials such as Hastelloy-C, X-alloy 306, Duranickel, etc., are recommended for those parts coming to contact with the polymer (inner surface of cylinder, screw, torpedo, nozzle, etc.). If not used as a machine exclusively for Fluon®ETFE, nitrided and hard-chromium-plated materials may also be used.

### (2) Mold

The mold used, although depending on the number of shots, should be hard-chromium-plated on ordinary materials, and must be designed to stand temperatures up to 120°C. The gate structure may be selected from side gate, pinpoint gate, film gate, etc., depending on the product desired. The runner is desired to be designed to have a round cross section, and as short a length as possible.

### (3) Molding Conditions

Table 20 outlines the typical conditions for molding Fluon®ETFE. For light-gage molding (thinner than 0.5 mm), the speed should be increased, while for heavy-gage molding (thicker than 5 mm), the cooling time should be increased. Furthermore, to obtain a smooth surface, the injection speed should be reduced.

**Table 20 Injection Molding Conditions for Fluon®ETFE**

		Natural Grade
Molding Temperature (°C)	Back	260~280
	Middle	270~290
	Front	280~300
	Nozzle	290~320
Mold Temperature (°C)		60~120
Injection Pressure (MPa)		50~120
Injection Speed (ram speed) (mm/sec)		1~15
Molding Cycle (sec)		30~120

Figures 69~71 show the relationship of molding temperature and fluidity, and Figures 72~73 show the relationship of various molding conditions and molding contraction.

Molding temperature and injection speed do not affect the fluidity much, but has the greatest effect on the surface smoothness.

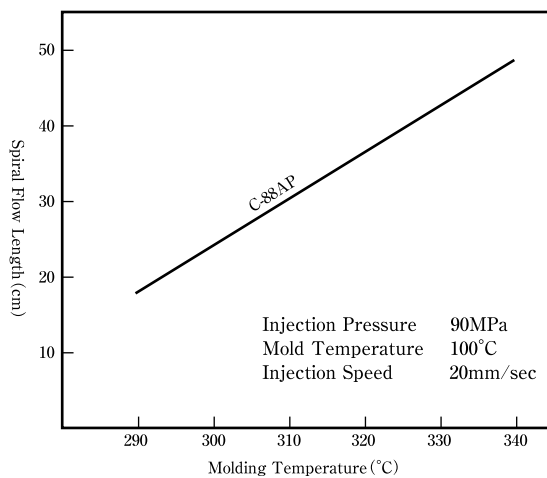


Figure 69 Molding Temperature and Spiral Flow Length

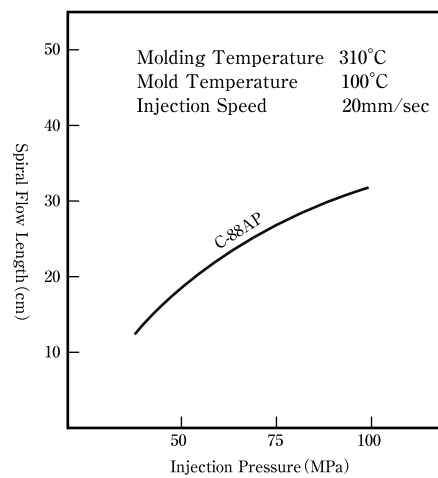


Figure 70 Injection Pressure and Spiral Flow Length

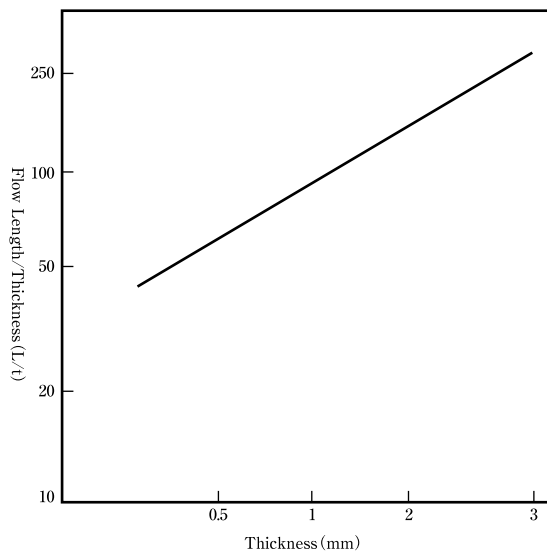


Figure 71 L/t and Thickness (C-88AP)

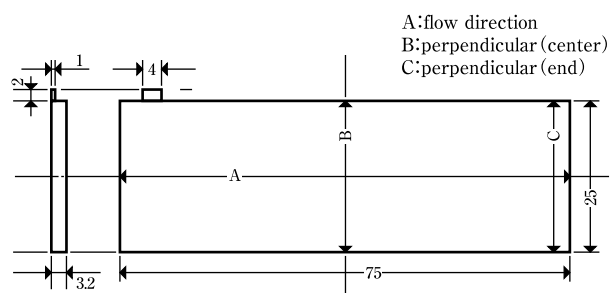


Figure 72 Cavity Scale of Mold (Unit : mm)

Because Fluon®ETFE is a crystalline polymer, the shrinkage is relatively large. The shrinkage was measured in the flow direction, and in the direction perpendicular to the flow, by using the mold shown in Figure 72.

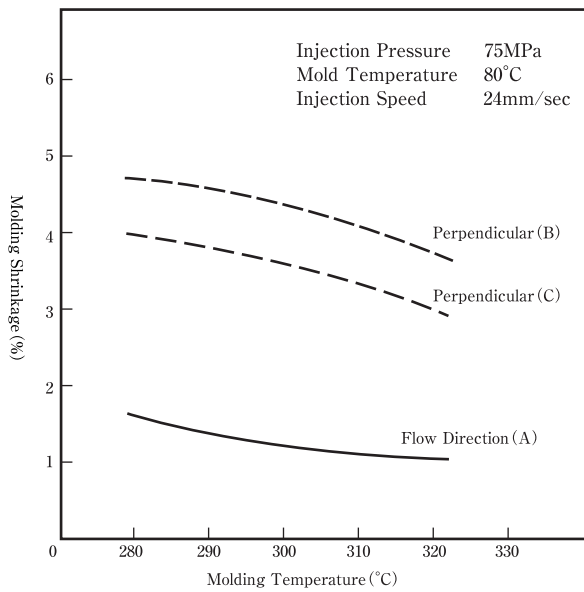


Figure 73 Molding Temperature and Molding Shrinkage

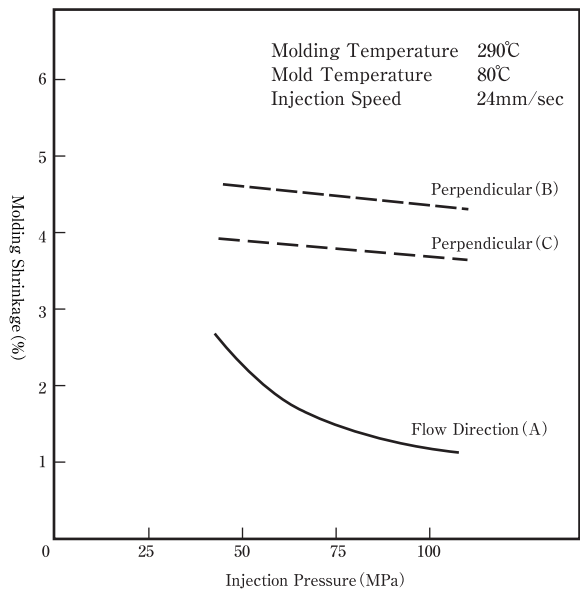


Figure 74 Injection Pressure and Molding Shrinkage

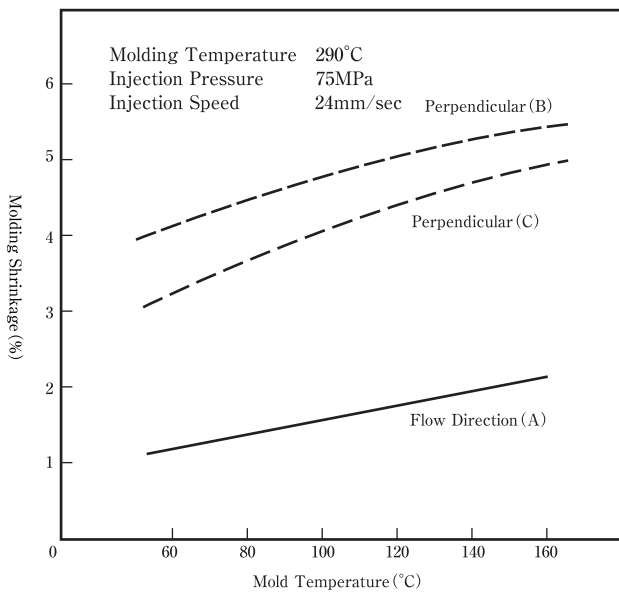


Figure 75 Mold Temperature and Molding Shrinkage

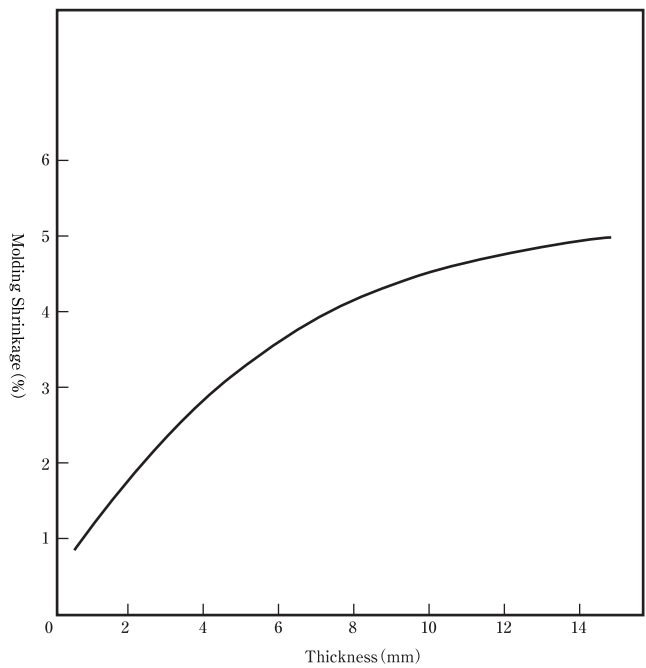


Figure 76 Thickness and Molding Shrinkage

The shrinkage of Fluon®ETFE natural grades (C-55AP, C-88AP, C-55AXP, C-88AXP), when molded under ordinary conditions, is 1.5~2.0% in the flow direction, and 3.5~4.5% in the perpendicular direction.

Table 21 Molding Contraction of **Fluon®ETFE**

	C-88A
Flow Direction (%)	1.5~2.0
Perpendicular to the Flow (%)	3.5~4.5

## 7-3 Extrusion Molding

Fluon®ETFE can be molded by extrusion into small diameter (up to 10mm $\phi$ ) rods, tubes, pipes, and electric wire coating, and by using the T-die, or by inflation molding, into films. Blow molding and uniform profile mold extrusion molding are also possible. Standard molding conditions are shown below.

**Table 22 Extrusion Molding Conditions for Fluon®ETFE**

	Specification	Electric wire Covering	Film	Tube
Extruder	Screw diam	40 mm $\phi$	40 mm $\phi$	35 mm $\phi$
	Screw type	metering	metering	metering
	Screw L/D	25	22	22
	Screw comp. ratio	2.6 : 1	2.8 : 1	2.5 : 1
	Screen	80, 100 & 200 mesh, 2 each	80, 100 & 200 mesh, 2 each	80, 100 & 200 mesh, 1 each
Die	Die i.d.	4.3 mm	Coat hanger type manifold die	13.5 mm
	Nipple o. d.	2.0 mm		12.1 mm
	Rand length	20 mm	Lip spacing 0.2 mm	
Product		core : tin-plated soft copper wire	film thickness : 25 $\mu$ m	tube i.d. : 9 mm $\phi$
		core diam : 0.26 mm $\phi$	film width : 400 mm	tube o.d. : 10 mm $\phi$
		thickness : 0.15 mm		thickness : 0.15 mm
		final diam : 0.56 mm $\phi$		
Molding conditions	Cylinder temp.			
	C1	250~260 °C	270 °C	270 °C
	C2	270~290 °C	290 °C	290 °C
	C3	330~340 °C	310 °C	300 °C
	Cross head	330~340 °C		
	Die	350~360 °C	315 °C	310 °C
	Air gap		80 mm	100 mm
	Draw down ratio	59		die diameter/sizing die diameter 1.35
	Pull speed	80~150 m/min	5 m/min, cooling roller temperature 120 °C	4 m/min vacuum sizing

## 7-4 Powder Coating

Powder coating methods such as electrostatic powder coating, fluid dipping, etc., can be used for Fluon®ETFE coating. The selection of the raw resin depends on the desired thickness and the application. The polymer is not hygroscopic, but the powder flow is affected by moisture content. Therefore, compressed air used for flowing should be dried prior to the process. Furthermore, as dust mixed in the polymer may cause pinholes or coloration, the package or the hopper should not be left open.

### (2) Pretreatment

Table 23 Pretreatment

Steel Material (Thick Lining)	Degreasing : baking 400°C× 2 hrs or more Coarsening : blasting with 60 mesh-pass steel grid and sand (jet pressure 3~7kg/cm <sup>2</sup> )
Steel, Stainless Steel, Aluminum (30~50μm)	Degreasing : washing with trichloroethylene Coarsening : blasting with 100 mesh-pass steel grid and sand (jet pressure 3~7kg/cm <sup>2</sup> )
Copper and Copper Alloy	At the time of baking, a fragile oxidation film is formed. Therefore, metal plating or copper oxide film treatment (5 min boiling in a mixture of 1 part potassium persulfate, 4 parts sodium hydroxide and 95 parts water) is carried out.
Glass	Silan coupling agent treatment [(1) washing, (2) dipping in 30% nitric acid at 60°C×2 hrs, (3) soaking in 1% ethanol solution of silane coupling agent (Union Carbide A-1120) for 24 hrs., (4) air drying, (5) coating]

### (3) Coating

Apply a voltage of 60~90 kV, using an electrostatic coating machine, and turn off immediately before inducing electrostatic repulsion. Film thickness of the 30~150μm for the natural grades, and 1mm for the ZL-520N by repeating 5~7 layers of coating, can be obtained. By the fluid dipping of Z-885A, a film thickness of 0.6mm can be obtained with a substrate of 5mm thickness, and preheating of 340~360°C.

### (4) Baking

Baking should be carried out at a temperature in the range of 290~340°C, for 10~16 minutes, depending on the thickness of the substrate, the material, and the desired film thickness.

### (1) Material and Shape of Substrate

As long as the material withstands temperatures in the range of 290~340°C, Fluon®ETFE can be coated, not only on metallic surfaces, but on glass and ceramics, as well. The edges tend to shrink in thickness upon solidification. Therefore, it is necessary to provide a roundness of 1R, in thin layer lining, and for thick linings of 0.4~1mm, 3R or larger at extrusions and 5R or more at intrusions.

### (5) Film Thickness Test

The film formed is tested by a method similar to the testing method for PTFE film, conforming to JIS K6894, as well as by other methods, such as the film thickness test, pinhole test, Erichsen test, corrosion resistance test, etc., depending on the application.

## 7-5 Other Processing

### (1) Welding of Fluon®ETFE

Fluon®ETFE can be welded using HOTJET (FUJI MFG Co., LTD. Sold by Tokuhara-Kiko Tel. +81-3-3563-1621).

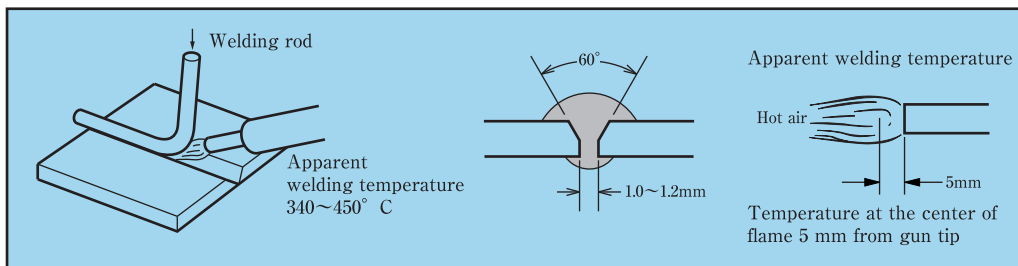


Figure 77

Welding requires a certain degree of skill, but by paying careful attention on the area to be welded, and by turning both the mother material and the welding rod into a waxy state, it is possible to obtain a strength equivalent to 60% that of the mother material, and achieve a welding speed of 80mm/min.

### (2) Flare Processing of Fluon®ETFE

A 90° flare processing of Fluon®ETFE pipes and injection moldings can be performed by using special tools. By heating the tool material at 130~150°C, flare processing may be done at a rate of 60mm/min.

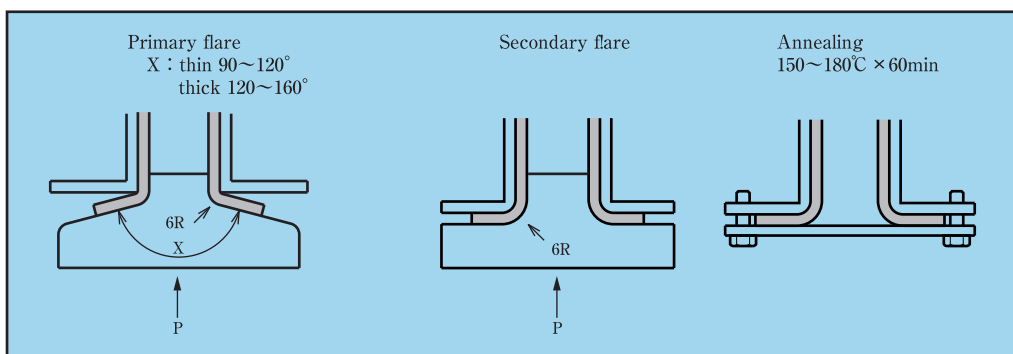


Figure 78

#### Notice

- 1) The statements and data given in this publication are believed to be accurate. They are presented without any guarantee or warranty, express or implied. Statements or suggestions regarding the use of these products are made without representation or warranty that any such use is free of patent infringement and are not recommendations to infringe any patent. The user should not assume that all safety measures are indicated.
- 2) Please refer to the MSDS (Material Safety Data Sheet) for safety and details.
- 3) This product is not designed for use in the implantation of the human body or for medical applications that come in contact with body fluid or body tissues, ASAHI GLASS CO., LTD. carries out no test as to the fitness of the product for any medical applications.
- 4) The contents are subject to change without prior notice.

---

### **AGC Chemicals, Fluoropolymers Group** **ASAHI GLASS CO., LTD.**

1-12-1, Yurakucho, Chiyoda-ku, Tokyo, 100-8405 Japan  
Phone : +81-3-3218-5875 Facsimile : +81-3-3218-7856  
URL <http://www.agc.co.jp/>  
Fluon Website <http://www.fluon.jp/fluon/english/>

### **AGC Chemicals Trading (Shanghai) Co., Ltd.**

Room 2307-2308, Rui An Plaza, 333 Middle Huai Hai Road, Shanghai, 200021 China  
Phone : +86-21-6386-2211 Facsimile : +86-21-6386-5377

### **AGC Chemicals Europe, Ltd.**

PO Box 4, Thornton Cleveleys, Lancashire, FY5 4QD UK  
Phone : +44-1253-861963 Facsimile : +44-1253-861950

### **AGC Chemicals Asia Pacific Pte., Ltd.**

460 Alexandra Road, #30-02, PSA Building, 119963 Singapore  
Phone : +65-6273-5656 Facsimile : +65-6276-8783

### **AGC Chemicals Americas, Inc.**

55 East Uwchlan Avenue, Suite 201, Exton, PA, 19341 USA  
Phone : +1-610-423-4300 Facsimile : +1-610-423-4301