

New HFO Blowing Agent with Excellent Performances

AMOLEA™ 1224yd

AGC

AMOLEA™ 1224yd is a blowing agent which is suitable for foam application where superior environmental, flammability, and foam properties are required.

Foam applications include polyurethane, polyisocyanurate, and various polymer foams.



AMOLEA™ 1224yd (HFO-1224yd(Z))

Molecular formula	(Z)-CF ₃ CF=CHCl
Molecular weight	148.5 g/mol
Boiling point	15 °C
Liquid density (25°C)	1,361 kg/m ³
Vapor pressure (25°C)	151 kPa
Thermal conductivity (gas, 25°C)	9.1 mW/m·K
Atmospheric Lifetime	20 days*
ODP (CFC-11=1)	0.00023*
GWP (IPCC AR5)	0.88*
LC ₅₀	213,000 ppm
AEL	1,000 ppm
Flammability (ASTM E681)	Non-flammable

Zero-ODP


*Measured by the National Institute of Advanced Industrial Science and Technology (AIST)

Your Dreams, Our Challenge

What is AMOLEA™ 1224yd?

Concepts

AMOLEA™ is a next-generation solvent and refrigerant brand developed by AGC under the concept of "dramatically reducing GWP with superior performance."

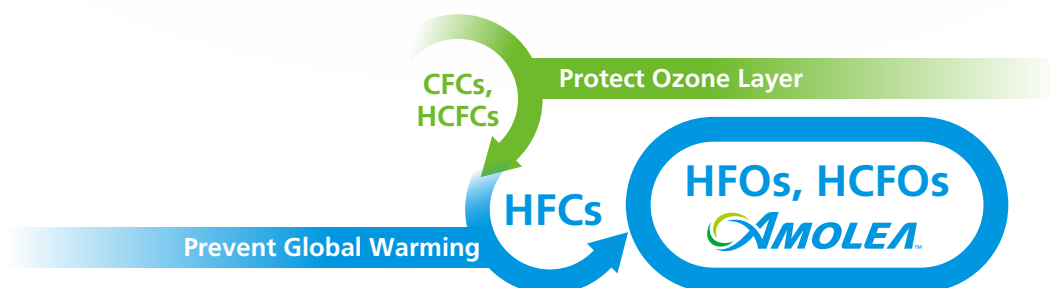


*AMOLEA™: AGC Makes Hydrofluoro-Olefins as Alternatives

Features

- Chemical and physical properties similar to HFC-245fa
- Good compatibility with plastics and elastomers
- Low thermal conductivity
- GWP under 1*
- Zero-ODP (0.00023 as CFC-11=1*)
- Low-toxicity ($LC_{50} > 213,100\text{ppm}$, $AEL=1,000\text{ppm}$)
- Non-flammable (ASTM E681)

*Measured by the National Institute of Advanced Industrial Science and Technology (AIST)

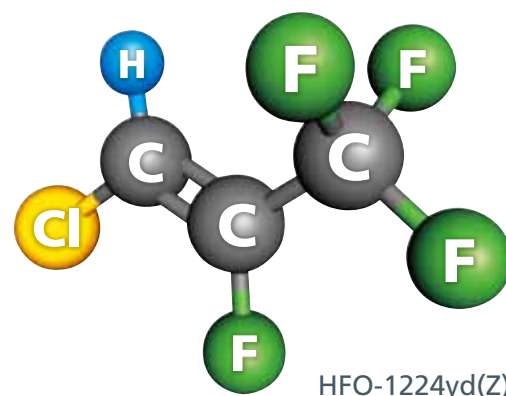


Application


- Blowing agent
- Aerosol solvent
- Solvent
- Centrifugal Chiller
- Organic Rankine Cycle (e.g. Binary cycle)
- High-temperature heat pumps

Properties

Vapor pressure

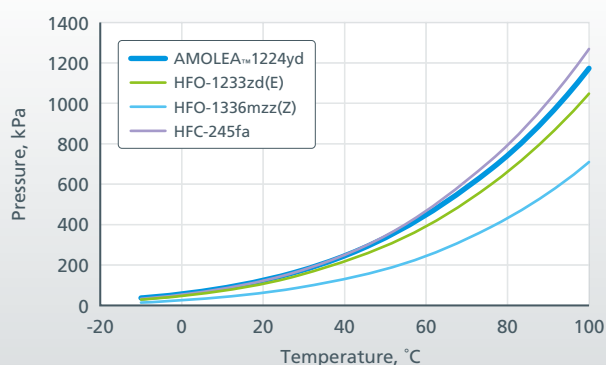

Thermal conductivity

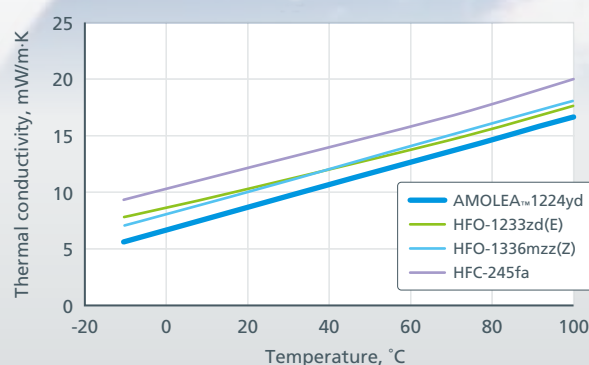

Material compatibility

Plastics				
Blowing agent	AMOLEA™ 1224yd		HFC-245fa	
Material	Weight change, %	Volume change, %	Weight change, %	Volume change, %
PVC (Rigid)	0	0	0	0
PVC (Soft)	-8	-12	N.D.	N.D.
LDPE	7	4	1	0
HDPE	4	3	N.D.	N.D.
Polypropylene	9	5	2	0
Polystyrene	11	8	0	0
Acrylic resin	Dissolved	Dissolved	Dissolved	Dissolved
Polycarbonate	1	1	0	0
Polyphenylene oxide	8	5	N.D.	N.D.
Phenolic resin	0	0	-1	0
ABS resin	9	6	2	0
Nylon 66	0	-2	-1	-1
Epoxy resin	0	0	0	0
PTFE	5	7	2	1

Elastomers						
Blowing agent	AMOLEA™ 1224yd			HFC-245fa		
Material	Weight change, %	Volume change, %	Elution %	Weight change, %	Volume change, %	Elution %
Natural rubber	2	-3	9	2	1	1
Silicone rubber	93	103	3	12	10	1
Urethane rubber	56	49	0	26	21	0
Butyl rubber	2	-3	13	-4	-6	5
Chlorosulfonated polyethylene rubber (Hypalon™)	11	9	5	-1	-3	2
Chloroprene rubber	6	3	11	-3	-6	6
EPDM	6	1	9	1	0	1
Nitrile rubber	2	-4	10	6	4	7
FKM	41	56	1	70	109	3
HNBR	18	9	12	21	14	10


Shelf stability study

(Rise time measurements)


Formulation		
Polyester polyol (OHV: 315mgKOH/g)	pbw	70
Polyether polyol (OHV: 590mgKOH/g)	pbw	30
TCPP	pbw	20
Surfactant SH-193	pbw	1.0
TEDA®-L33	pbw	10.0
Water	pbw	1.0
Blowing agent	pbw	0.218mol
Polymeric MDI	pbw	171.9
INDEX		160

Foam condition
Hand Mix Foaming, Mixing Conditions: 3000rpm×5sec, Component Temp. :15°C

Component Storage Temp. :23°C

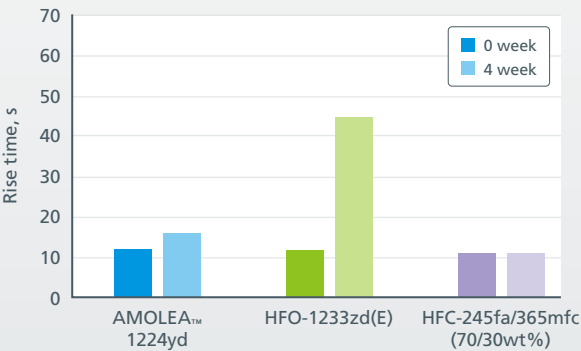


Component Storage Temp. :40°C

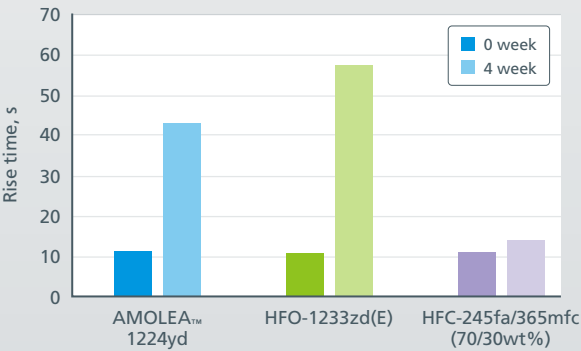


Polyurethane spray foam

Blowing agent	AMOLEA™ 1224yd	HFO-1233zd(E)	HFO-1336mzz(Z)	HFC-245fa/365mfc (70/30wt%)
Formulation				
OHV	mgKOH/g	590	590	590
Polyether polyol	pbw	100	100	100
TCPP	pbw	20	20	20
Surfactant SH-193	pbw	1.0	1.0	1.0
POLYCAT® 41	pbw	0.5	0.4	0.5
PUCAT 15G (K15%)	pbw	0.5	0.4	0.4
Water	pbw	1.0	1.0	1.0
Blowing agent	pbw	32.5	28.5	35.6
Polymeric MDI	pbw	173.3	173.3	173.3
INDEX	110.0	110.0	110.0	110.0
Foam properties				
Reaction time	c.t., s	12	12	12
	g.t., s	32	31	32
	r.t., s	39	38	40
Foam density	kg/m³	32.0	33.8	32.5

Foam condition
Hand Mix Foaming, Mixing Conditions: 3000rpm×5sec, Component Temp. :15°C
Thermal conductivity measurement
Sample size: 190×190×25mm, Condition: Mean Temp. :23°C, according to JIS A9511

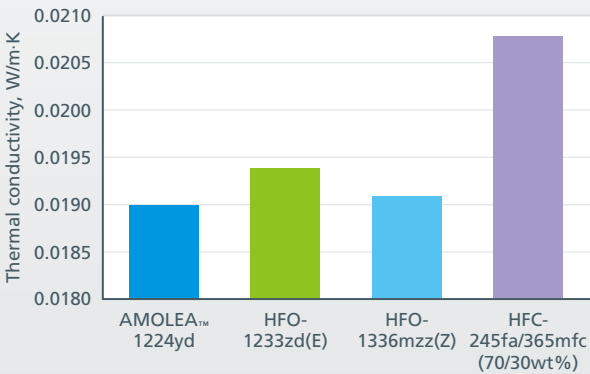

Foam Storage Temp. :70°C

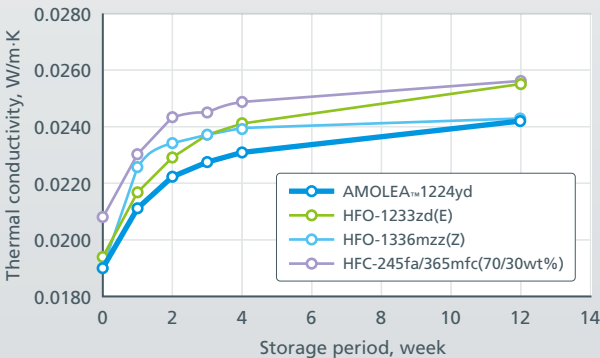

Environmental Impact

Blowing agent	HFOs			HFC
	AMOLEA™ 1224yd	HFO-1233zd(E)	HFO-1336mzz(Z)	HFC-245fa
AEL, ppm	1,000	800	500	300
ODP	0.00023*	0.00024	0	0
GWP (IPCC AR5)	0.88*	1	2	858
MOP HFC regulation	N.A.	N.A.	N.A.	Applicable
EPA-SNAP	Applying	Registered	Registered	To be delisted
REACH	Registered	Registered	Registered	Registered

*Measured by the National Institute of Advanced Industrial Science and Technology (AIST)

Contacts

AGC Inc.
AGC Chemicals
1-5-1, Marunouchi Chiyoda-ku Tokyo 100-8405 Japan
Tel: +81-3-3218-5875
www.agc.com

AGC Chemicals Americas, Inc.
55 E. Uwchlan Avenue Suite 201 Exton, PA 19341 USA
Tel: +1 610-423-4300
www.agcchem.com

AGC Chemicals Europe, Ltd.
Commercial Centre
World Trade Center Zuidplein 80
1077 XV Amsterdam Netherlands
Tel: +31 20 880 4170
www.agcce.com

AGC Chemicals RUS
Russian Federation, 121596 Moscow, Gorbunova Street 2
Grand Setun Plaza, Bldg. 204, BC
5th Floor, Block B, Office B 504
Tel: +7 918 555 34 37
www.agcce.com/главная

AGC Chemicals South America
Al. Min. Rocha Azevedo 38/1004
01410-000 São Paulo Brazil
Tel: +55 11 3373-9994
www.agcbrasil.com

AGC Asia Pacific Pte. Ltd.
460 Alexandra Road #30-01 PSA Bldg.
Singapore 119963
Tel: +65-6273-5656
www.agc.com

AGC Chemicals Trading (Shanghai) Co., Ltd.
Room 2701-2705, Metro Plaza
555 Lou Shan Guan Road
Chang Ning Ward, Shanghai China 200051
Tel: +86-21-6386-2211
www.agcsh.com

AGC Chemicals (Thailand) Co., Ltd.
24th Floor Bangkok Insurance Bldg.
25 South Sathorn Road Bangkok 10120 Thailand
Tel: +66-2-679-1600
www.acth.co.th